

Transforming pangasius catfish waste into innovative nano particles: Elevating fish gelatin from derivative to product enhancement

Yoni Atma^{a,b,*}, Nina Jusnita^c, Susiana Melanie^{d,e}, Moh Taufik^f, Muhammad Yusuf^{g,h}

^a School of Food Science and Nutrition, University of Leeds, Leeds, LS9 2JT, United Kingdom

^b Department of Food Science and Technology, Universitas Trilogi, South Jakarta, 12760, Indonesia

^c Department of Pharmacy, Universitas 17 Agustus 1945, North Jakarta, 14350, Indonesia

^d Department of Materials, Imperial College London, London, SW7 2AZ, United Kingdom

^e Research Center for Polymer Technology, Research Organization for Nanotechnology and Material (ORN), National Research and Innovation Agency (BRIN), South Tangerang, 15314, Indonesia

^f Food Technology, Department of Science and Technology, UIN Raden Mas Said Surakarta, Sukoharjo, 57168, Indonesia

^g School of Chemical and Process Engineering, University of Leeds, Leeds, LS9 2JT, United Kingdom

^h Research Center for Nuclear Materials and Radioactive Waste Technology (PRTBNLR), Research Organization for Nuclear Energy (ORTN), National Research and Innovation Agency (BRIN) South Tangerang 15314, Indonesia

ARTICLE INFO

Keywords:

Biophysical characterization

Fish gelatin

Fish processing by-products

Nanocomposites

Nanoparticles

Fish gelatin, derived from processing by-products, has captured substantial attention due to its sustainability and exceptional attributes. This comprehensive review explores its multifaceted applications, with a special emphasis on the potential of Indonesian Pangasius catfish as a source, showcasing its superior properties and innovative pre-treatment techniques. However, the exploration of fish gelatin at the nano scale remains a largely uncharted territory. In general, interdisciplinary approaches and diverse synthesis methods, such as desolvation and electrospinning, have recently unveiled the vast potential of fish gelatin nanoparticles (NPs). These nanoparticles (NPs) serve as versatile carrier agents, biomaterials, and crucial components in antimicrobial packaging, drawing from various fish species. Furthermore, fish gelatin NPs have seamlessly integrated into nanocomposite (NC) films alongside substances like organic and inorganic NPs, promising significant strides in food safety and preservation strategies. Remarkably, fish gelatin NPs exhibit unique antimicrobial properties, positioning them as promising candidates for applications in both the food packaging industry and biomedicine. Moreover, the inclusion of NPs enhances mechanical performance, augmenting their suitability for a multitude of applications. This review highlights transforming and elevating of Pangasius catfish gelatin-based NPs, drawing inspiration from techniques applied to other fish species. It underscores the imperative need for systematic optimization encompassing gelatin extraction, synthesis, and characterization. Additionally, it addresses the formidable challenges and promising opportunities associated with unlocking the full industrial potential of gelatin-based NPs, thereby pointing towards a sustainable and innovative future in the field of materials science. Readers are cordially invited to embark on this promising avenue of research, where a world of possibilities awaits exploration and the promise of environmentally friendly innovation beckon.

1. Introduction

Gelatin has been widely used in food, pharmaceutical, cosmetic, and photographic industries. In food industry, gelatin is used as emulsifier, stabilizer, thickener, biodegradable film, foaming, gelling as well as encapsulation agents and it is estimated around 52% from total gelatin production worldwide. According to market share value, gelatin is the highest among most important hydrocolloid material for food application reaching 21.2% [1]. Indonesia has been imported gelatin to supply

the national demand reaching 4,250,933 kg per year or with import worth of US\$ 30,136,022 per year in average (2014–2018) [2]. Most of gelatin is imported from Brazil, India, China, United States, and Australia. In addition, majority of gelatin derived from pig skin (44%), bovine hides (28%), and bovine bones (27%) [3]. However, this mammalian sources have some obstacles related with religion, socio-cultural, health aspects, and virus outbreaks. Therefore, it is urgently needed an alternative gelatin replacing mammalian traditional gelatin. Gelatin from fish processing by-products especially skin and

* Corresponding author. School of Food Science and Nutrition, University of Leeds, Leeds, LS9 2JT, United Kingdom.

E-mail addresses: yoniatma@trilogi.ac.id, fsya@leeds.ac.uk (Y. Atma).

<https://doi.org/10.1016/j.mtsust.2024.100750>

Received 12 October 2023; Received in revised form 17 February 2024; Accepted 14 March 2024

Available online 15 March 2024

2589-2347/© 2024 Elsevier Ltd. All rights reserved.

bone are most potential alternative gelatin [4–7] which accepted universally with respect to those the aspects mentioned.

The by-products from fish filleting process are approximately 70% [8] from total of fish weight and around 30% fish weight could be derived from skin and bone [9,10]. The others convey that the fish waste portion from fishery commodities are more than 21% [11]. Ministry of Marine Affairs and Fisheries outlined that fish production in Indonesia in 2015–2017 was 11.042 billion tons per year which divided into marine capture fish, freshwater fish, and farmed fish [12,13]. So that, the fish processing by-products particularly skin and bone is estimated around 3.512 billion tons per year. If we assumed that the gelatin yield from fish waste adopted from previous research was 2.4% (the lowest yield) [14, 15], means that it would produce as many as 87.675.177 kg gelatin or would be more than 20-folds higher than the national (Indonesia) need. Furthermore, the fish gelatin from warm-water fish have superiority in term of physical properties compared to cold-water fish [16–18]. Thus, it will be potential to developed in the future including to export goal.

The *Pangasius catfish*, *Pangasius sutchi* (*P. sutchi*), or *P. hypophthalmus* syn. or *P. gigas* commonly known as Patin, holds a prominent position within Indonesia's flourishing fisheries sector, making a substantial contribution to an annual production exceeding 300,000 tons [19,20]. This indigenous piscine species undergoes diverse processing, resulting in an assortment of products encompassing Patin fish fillets, traditional culinary offerings, and a variety of derived edibles. This extensive utilization inevitably leads to the generation of associated by-products, among which fish bones assume significant proportions, accounting for no less than 23–27% of the fish's total weight [21]. Given the scale of its annual production, this implies a potential accumulation of over 69,000 until 81,000 tons of Patin bones as residual waste on a yearly basis. Considering mounting environmental concerns, the imperative to develop technology aimed at managing and mitigating the disposal of Patin bone waste becomes paramount.

Similar to *Pangasius catfish*, *Pangasius bocourti* is a type of freshwater fish which also belonging to the Pangasidae family [22] and is known as basa catfish [23]. Basa catfish is the preferred variety of *Pangasius* because it has whiter flesh color [24], smooth texture [25], sweet taste, and does not have a fishy or spiny smell [26]. This fish has been exported to more than 100 countries around the world [24] in fillet form [22]. Processing these fish produces large amounts of waste such as viscera, skin, scales, bones, and skeletons [27]. Le Thi (2017) [28] explained that the number of by-products from Basa fish processing was 59%. Proper processing is needed to convert these by-products into products that have high economic value [24]. Two products resulted from processing basa catfish waste are fish oil [29] and gelatin [30,31]. Yet, the Basa catfish was not popular compared to *Pangasius catfish*, especially in Indonesia. The *Pangasius catfish* has been produced around 380,000 tons annually by 2022, which causing the *Pangasius catfish* farming industry also presents a chance for more significant financial gain compared to Basa fish [32].

Until the 20th century, gelatin's historical role, predominantly revolved around its essential application in the realm of food products, a role of undeniable historical significance. However, this role, though foremost, is merely the tip of the iceberg [33]. Gelatin's versatility extends well beyond the culinary domain, finding its utility in addressing a myriad of challenges posed by human activities. It has become a key player in diverse fields, including its crucial involvement in adhesive formulations for artistic creations using materials like wood, leather, textiles, and publications. Additionally, gelatin plays a pivotal role in the formulation of water-soluble coatings for washing and dishwasher tablets and serves as a critical component in ballistic testing, famously recognized as ballistic gelatin [34–36].

While these applications span various sectors and possess distinct characteristics, they share a common thread anchored in macro-level

gelatin structures' mechanical and physical attributes. However, limited attention has been paid to exploring the potential of fish gelatin at the micro- and nanoscale levels, specifically focusing on its molecular properties and structural organization. The nanoscale dimension unveils exciting opportunities for leveraging gelatin's unique characteristics, leading to a diverse range of applications. For example, gelatin plays a crucial role in nano particle synthesis and immobilising nano particles containing a wide array of chemical compounds [34,37,38]. The development of gelatin can be found in medical applications by encompassing capsules from fish gelatin, components of nutrient mixtures, culture media, and essential elements in plasma-substituting and diagnostic tools [38–41]. Also, Gelatin-based nanomaterials find extensive utility across various domains, particularly within protein-based nanotechnologies [42–44]. More extensive details of fish gelatin preparation until the use of enhancements from nanomaterials productions are described in the next sections.

Definitely, gelatin NPs have garnered prominence in food applications, marking a significant stride in integrating nanotechnology into culinary endeavors [45–47]. Given gelatin's historical lineage, rooted in its chemical properties, this discourse primarily delves into the first application area: photographic gelatin. The second application area emerges as a logical extension, as silver halide photographic materials frequently constitute the foundational elements of gelatin-immobilized systems. Notably, these systems often exhibit nanostructural organization, thereby augmenting their significance. The third application, centered on medical purposes, assumes pivotal importance in contemporary practice, particularly within the medical domain, warranting substantial attention, as emphasized earlier. The fourth facet relates to the utilization of gelatin in NP form, pertinent to diverse nanotechnological pursuits.

The utilization of fish by-products for nano gelatin production presents a diverse spectrum of possibilities [48–50]. These resources, comprising elements from warm and cold aquatic realms, have demonstrated distinct variations in gelatin attributes. Gelatin sourced from warm-water fish, exemplified by the *Pangasius catfish* bone gelatin, exhibits remarkable gel strength akin to mammalian-derived gelatin. This advancement in the knowledge of fish gelatin properties offers substantial insights for various applications within the gelatin industry and beyond.

In this study, we emphasize a novel approach to utilizing gelatin obtained from the by-product of Patin as a key component in producing gelatin-based nanoparticles (NPs), nanofibers (NFs), or nanocomposites (NCs). This not only addresses the waste management issue within the catfish industry but also enhances the functionality of the resulting nanomaterials.

One of the unique aspects highlighted in this review is the multitude of benefits derived from gelatin extracted from fish waste, specifically Patin, and the various products that can be developed and potentially applied to industrial levels. The review outlines the work conducted by researchers on the extraction of gelatin from Patin processing by-products and the subsequent possibility on enhancement of its value into NPs, NFs, or NCs. It delves into the approaches that can be employed in synthesizing gelatin-based nanomaterials, as well as the standard characterization and functionality testing methods (summarized at Fig. 1). Additionally, the review offers simulation approaches that can be applied to enhance the value of fish processing by-products, making it market-ready, along with the challenges and opportunities that must be addressed. Overall, this review presents a comprehensive examination of the utilization of gelatin derived from Patin waste, showcasing its potential in the development of various nanomaterials and addressing both waste management concerns and functional enhancement requirement.

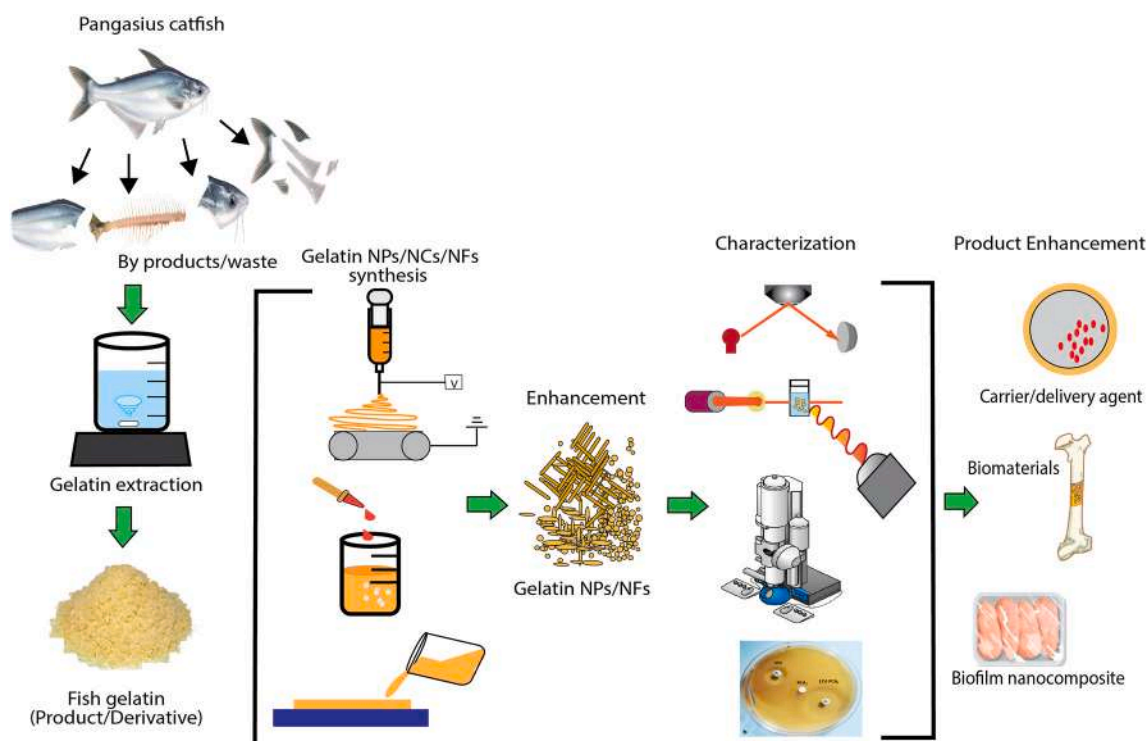


Fig. 1. Transformation of Pangasius catfish gelatin, minimizing waste and enhancing product efficacy through nanotechnology integration.

2. Fish gelatin and pangasius catfish gelatin

The published work related to fish gelatin is mainly focused on their extraction process or optimization of extraction, and characterization of obtained fish gelatin. The extraction process normally comprises two main stages: pre-treatment and main extraction. The pre-treatment commonly involves soaking the raw material (fish bones, skin, or fish waste) under certain conditions for example in the acid [51–54], alkaline [55,56], or weak acid solvent [57,58]. Subsequently, the main extraction is carried out using a combination of acid, alkaline [59,60], water [14,56,61] and ultrasound assisted [62]. In terms of characterization, a significant portion of the research analyzes the yielded gelatin [63,64], examines its chemical composition (with a primary focus on proximate analysis and amino acid composition) [65,66], and assesses its physical characteristics such as texture profile (particularly gel strength) and viscosity [55,56,67].

Various types of fish parts, such as their skin, bones, and another by-product, have been harnessed as sources of gelatin. Broadly, they can be categorized into marine and freshwater fish, sourced from warm and cold aquatic regions [68–71]. Research findings indicate that gelatin derived from warm-water fish exhibits enhanced physical attributes, such as superior on gel strength, thermostability, and viscosity, when compared to gelatin sourced from cold-water counterparts [6, 72–74]. Among warm-water fish, the studies for gelatin production were covering Tilapia [15,75], certain parts of shark cartilage (*Isurus oxyrinchus*) [76], cod head [77], lizardfish scale (*Saurida tumbil*) [78], king weakfish (*Macrodon ancylodon*) [72], catfish (*Clarias gariepinus*) [54], Tuna [61], and Pangasius catfish (*Pangasius sutchi*) [14,67]. Notably, gelatin extracted from the bones of the Pangasius catfish stands out with its elevated yield among these warm-water sources. Mahmoodani's (2014) [53] research underscores that the gel strength of Pangasius catfish bone gelatin is on par with gelatin from mammalian sources. Indeed, gel strength is one of essential physical characteristic of gelatin. Furthermore, ash content of gelatin from this fish was 2.6 which is commercial gelatin have ash content $\leq 2.6\%$ [66].

Research on gelatin extracted from Pangasius catfish has been

conducted by several teams. Mahmoodani et al. (2014) [53] performed gelatin extraction from Pangasius catfish bones using strong acid in the pre-treatment stage, followed by main extraction with distilled water. The extraction process was optimized using the statistical response surface methodology (RSM). Ratnasari et al. (2013) [71] extracted gelatin from Pangasius catfish skin using citric acid for pre-treatment and distilled water for the main extraction. A study conducted by See et al. (2010) [59] focused on gelatin extraction from the skin of Pangasius catfish, utilizing acetic acid for pre-treatment and distilled water for the main extraction.

In Indonesia, studies on gelatin from Pangasius catfish have also been carried out. For instance, a study reported that the bone enables to produce gelatin. Pangasius sutchi's bone was separated from other waste materials like the head, fin, scales, and viscera. The attached flesh was scraped off the bones with a knife and then easily removed by soaking them in warm water (80–90 °C) for 30 min. Fish bones were subsequently washed with tap water and kept in the freezer (−20 °C) for a month. In the pretreatment stage, cleaned bones were minced in a meat grinder before being soaked in four different citrus fruit extracts with a bone solvent ratio of 1:5 (w/v). With varying times (24, 36, 48, and 56 h) to allow for demineralisation, pretreatment was done at room temperature. The leached bone (ossein) was then separated from the citrus fruits (pretreatment solvent) by centrifugation for 10 min at $10,000 \times g$ 4 °C. The ossein was washed in distilled water until the pH level reached ~ 7 , neutralising the protein. Following that, for the main extraction stage, the neutralised ossein was diluted 1:5 with water. Various temperatures (45, 55, 65, and 75 °C) were used during the main extraction, lasting 5 h [63]. Gelatin extraction from Pangasius catfish bones also involved pre-treatment using citric acid [57], acetic acid [79], and pineapple waste [14,80]. During the pre-treatment stage using pineapple waste, liquid waste was pasteurized to prevent gelatin hydrolysis due to the presence of the bromelain. In these studies, the presence of gelatin had identified based on molecular weight (Mw) using sodium dodecyl sulphate polyacrylamide gel electrophoresis (SDS-PAGE) and specific amino acid percentage, the hydroxyproline. In addition, beside the yield analysis, the study also measured the physical properties of the

Table 1
Extraction gelatin from waste of *Pangasius catfish*.

Fish waste	Extraction Process		Yield (%)	Gel strength (g.Bloom)	Ref.
	Pre-treatment	Main extraction			
Bone	Hydrogen chloride for 21 h.	Distilled water at 74.7 °C for 5.26 h	13.86	254.7	[53]
Bone	Citric acid for 48 h.	Distilled water at 75 °C for 5 h	6.14	364.19	[57]
Skin	Sodium chloride at 5 °C for 10 min.	Distilled water at 45 °C for 18 h	10.78	324.53	[59]
Bone	The Citrus fruit extract	Water at 55° for 5 h	6.26	451	[63]
Skin	Sodium hydroxide and acetic acid	Distilled water at 63.7 °C for 2.41 h	23.61	438.34	[67]
Skin	Sodium hydroxide followed by acetic acid	Distilled water at 50 °C.	24.65	105.30	[79]
Skin	Distilled water, lime, and followed by tamarind.	Distilled water at 50 °C for 12 h	19.72	282.29	[83]
Skin	Immersed in solution containing papain for 25 min	Distilled water at 80 °C for 3 h	4.97	115.17	[84]
Skin	Sodium hydroxide for 1 h	Distilled water at 65 °C for 8 h.	18	220.93	[85]
	Citric acid for 12 h.				
Bone	Hydrogen chloride for 48 h	Distilled water at 70 °C for 5 h	3.04–5.33	74.1–173.94	[86]

obtained gelatin, such as texture profile and gel strength [63,80].

Skin is another *Pangasius* waste product that can be converted into gelatin. Reported by Azizah et al. (2020) [81], the *Pangasius (Hypophthalmus)* skins were kindly provided by a pangasius fillet company in Karawang, Jawa Barat, Indonesia, and transported to the lab while chilled on ice. The skin preparation was followed based on modification from Zhang et al. (2016) [82]. The pangasius skin was squared off (1 cm × 1 cm) and then washed with tap water. For 12 h, the skin was submerged in a 0.25% citric acid solution at a skin-to-solution ratio of 1:4 (w/v). Deionised water (DI) was used to wash the skin, and it was then extracted at 65 °C for 7 h using a 1:1 (w/v) solution ratio and the skin. The product of the extraction process was filtered through two layers of cheesecloth to create a gelatin solution. To turn the gelatin solution into gelatin powder, it was dried in an oven at 50 °C for 15 h. The yield of gelatin from the extracted pangasius skin was $15.07 \pm 1.45\%$ in comparison to the starting material, a figure that is comparable to the (6–19%) reported by Karim and Bhat (2009) [7]. According to See et al. (2010) [59], the yield was 10.78% when the skin was removed over 18 h at 45 °C. The type of raw material, the pretreatment procedure, and the extraction temperature are key variables that can affect the yield values.

However, study on *Pangasius catfish* gelatin or fish gelatin in Indonesia remains quite limited. To our knowledge, no published work has progressed to the stage of fish gelatin application, let alone its development as NPs. Table 1 presents gelatin from *Pangasius* sp., the extraction techniques, and the gelatin properties.

3. Fish gelatin NPs: the state of the art

3.1. Exploration of fish gelatin in nanomaterials: synthesis and applications

In the current era, globally, fish gelatin has been tried to be studied for its development at the nano scale, both as a raw material in the form of gelatin NPs and in composite form with other substances, for the synthesis of carrier or delivery agents, biomaterials, metal catalysts, and antimicrobial film packaging (Fig. 2). Some fish species have been explored for the extraction of gelatin as a precursor to nano-products, encompassing *Tilapia* [87–91], *Mirror carp* [92], *Tuna* [93] and *Wall-eye pollock* [17]. However, certain investigations employing gelatin from cold-water fish fail to specify the exact fish species. Studies undertaken by Subara et al. (2017) [88] and Khramtsov et al. (2021) [94] have ventured into developing fish gelatin NPs from *Tilapia* skin and cold-water fish, respectively.

Furthermore, studies conducted by Hani et al. (2016) [90] and Akbar et al. (2020) [87] have respectively delved into gelatin nanofibers (NFs) and gelatin NPs sourced from *Tilapia* skin, employed as carrier agents for *Moringa oleifera* bioactive extract and sunflower-derived biopeptide, respectively. Fish gelatin-based NPs as carrier agents have also been investigated to enhance the bioavailability of polyphenols, with the latter the study employing hybridization of fish gelatin with

chitoooligosaccharide [95].

The evolution of fish gelatin into the nano realm represents a significant stride in contemporary scientific exploration. This trend has witnessed the utilization of diverse fish species, notably *Tilapia* and cold-water fish [94,96,97], as potential sources for the extraction of gelatin NPs. Furthermore, these NPs are being harnessed for various applications, including their role as carrier agents for bioactive substances [87,90,95], thereby accentuating their relevance in fields spanning biomedicine to sustainable packaging solutions. The ongoing research in this domain underscores the interdisciplinary nature of such studies, bridging the realms of biology, materials science, and nanotechnology to unlock innovative frontiers in sustainable materials and advanced functional systems.

The development of bionanomaterials based on fish gelatin has also been explored. For example, a study on bio-nanocomposite (NC) membranes composed of gelatin from tuna fish skin crosslinked with chitosan and tripolyphosphate (TPP) for applications in biomedicine and tissue engineering was conducted by Dara et al. (2021) [93]. Similarly, research performed by Nerjiang (2023) [92] focused on gelatin NPs derived from the skin of Mirror carp (*Cyprinus carpio*) fish to produce composite films with mechanical properties resembling collagen films. Furthermore, investigations into fish gelatin nanofibrous webs sourced from cold-water fish were undertaken to compare their adhesion capabilities, compatibility, and proliferation in relation to both bulk fish gelatin and mammalian gelatin [96]. Notably, Wu et al. (2015) [98] synthesized colloidal complex NPs from hydrolyzed gelatin extracted from fish bones, which were self-assembled with tannic acid. This effort aimed at developing materials with the potential to coat intestinal epithelial cells, particularly targeting the Tight Junction (TJ) regions.

The realm of bionanomaterials derived from fish gelatin represents a dynamic frontier in contemporary research. The utilization of fish-derived gelatin in the creation of composite membranes and NPs for diverse applications showcases the adaptability and versatility of this biomaterial. Moreover, the exploration of mechanical properties in composite films and the assessment of adhesion and compatibility underscore the pivotal role of fish gelatin in constructing materials that closely emulate natural counterparts. The synthesis of complex NPs for cellular interaction signifies a significant stride toward functional coatings with potential implications in biotechnological and medical contexts. This interdisciplinary approach intertwines materials science, biology, and nanotechnology, propelling the development of innovative solutions with broad-reaching applications. Table 2 presenting fish gelatin as NPs, carrier agent and biomaterial.

By thinking out of the box, the study conducted by Sinha et al. (2021) [100] capitalizes on the utilization of gelatin sourced from *Labeo rohita* scales as a reduction and stabilization agent in the synthesis of silver (Ag) NPs. Although, the gelatin was not used as source of nanomaterial, but their role had surprised us as readers. In this study, the synthesis procedure strategically hones in on the optimization of critical reaction parameters, encompassing temperature, pH, and extract concentration,

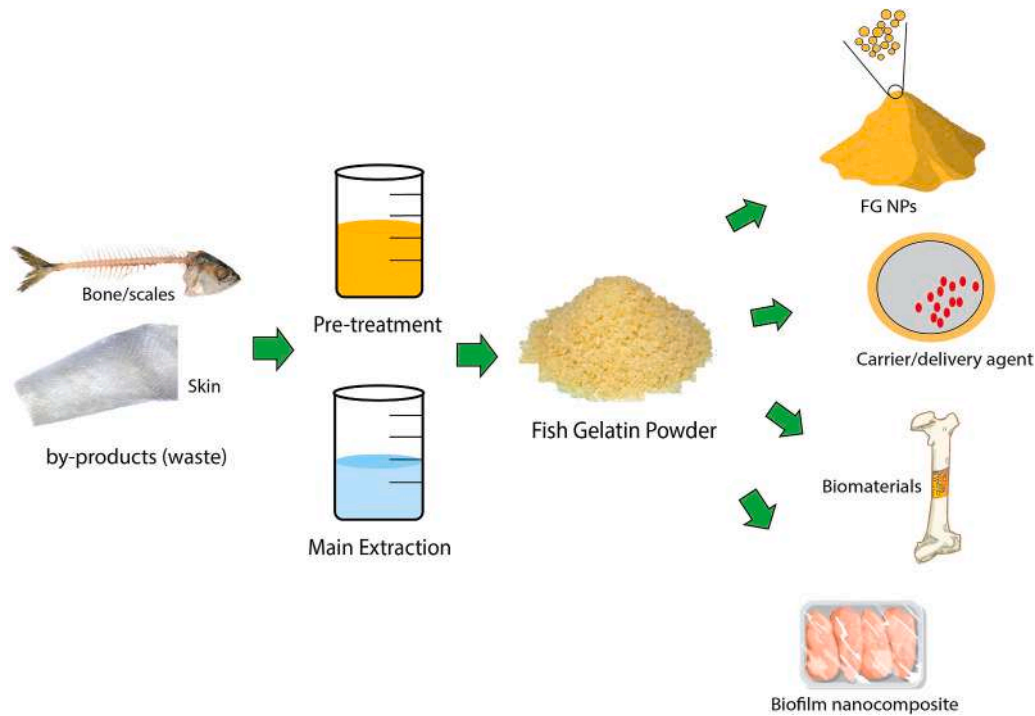


Fig. 2. Fish Gelatin NPs for different applications.

Table 2
Fish gelatin as NPs, carrier agent, and biomaterial.

Purposes	Form of Gelatin	Composite	Source of Fish Gelatin	Technique for production	Size of NPs	Size Measurement Principle	Other Characterization	Ref.
As Raw Material	Fish gelatin NPs (Single-component particles)	–	Tilapia fish skin	Two-step Desolvation	254 nm	Dynamic light scattering (DLS)	Scanning-Electron microscopy (SEM)	[99]
	Fish gelatin NPs (Single-component particles)	–	Cold water fish	One-step Desolvation	151–164 nm	DLS, TEM (Transmission Electron Microscopy)	SEM	[94]
Carrier	Gelatin NFs	–	Black Tilapia skin	Electrospinning + crosslinking	40–120 nm	TEM, SEM (diameter distribution)		[90]
	GNPs	–	Tilapia	Two Sstep dissolution	228–1305 nm	DLS	SEM	[87]
	FG/Chitooligo-NPs	–	Not reported detail	Maillard reaction	65.2–158 nm	DLS	SEM	[95]
Biomaterial	Fish gelatin hydrolyste Hybrid NPs	Tannic acid	Not reported detail	Coacervation	260.8 nm	DLS, TEM		[98]
	Fish gelatin nanofibrous	–	Cold water fish	Electrospinning + crosslinking	Diameter 91.42–200.48 nm	SEM		[96]
	Fish gelatin NC membrane	Chitosan + TPP	Tuna skin	Solvent Casting and Freeze-Drying Method	83–193 nm	DLS	SEM	[93]
	Fish gelatin NPs	Glutaraldehyde	Mirror carp skin (<i>Cyprinus carpio</i>)	Two-step desolvation	~155–410 nm	DLS	SEM	[92]

to exert precise control over the synthesis of Ag NPs. The resultant Ag NPs are subjected to meticulous investigation, particularly concerning their catalytic efficacy in the reduction of aromatic nitro compounds in both aqueous and micellar environments. Remarkably, the involvement of fish-derived gelatin introduces a complex interplay within this synthesis process. This intricate dynamic manifests as the gelatin from *L. rohita* scales engages in a multifaceted interaction with the silver ions, thereby acting as a dual role player. Primarily, it serves as a reductive agent, facilitating the conversion of silver ions into their metallic nanoparticulate form. Concurrently, the gelatin imparts an invaluable protective facet by enveloping the AgNPs, effectively establishing a

biomolecular corona. This biomolecular corona furnishes a dual-functionality shield; it augments the generation of Ag NPs by providing the requisite electrons for their reduction while simultaneously functioning as a protective layer, forestalling the premature aggregation of the resultant metallic NPs.

The synthesis of NCs for film applications, particularly in the realm of antimicrobial packaging, based on fish gelatin has garnered significant research attention. A substantial portion of these investigations involves the composite integration of fish gelatin with Zinc Oxide (ZnO) or ZnO NPs [17,89,91,101]. Additionally, some composites incorporate the biopolymer chitosan, while others feature a combination of

Silver–Copper (AgNPs and CuNPs) [102]. In assessing the potential of these nanofilms as antimicrobial agents, evaluations are conducted to ascertain their capacity to inhibit the growth of both gram-positive and gram-negative spoilage microorganisms.

Noteworthy studies undertaken by Arfat et al. (2015) [91], Arfat et al. (2016) [103], and Zhang et al. (2017) [89] have respectively synthesized nanofilms from Tilapia fish gelatin, incorporating zink (ZnO) NPs in tandem with fish protein isolate (FPI), and ZnO NPs + ginger oil respectively. Additionally, Hosseini et al. (2015) [104] and (2016) [97] have contributed to the field by fabricating NC films using cold-water fish gelatin reinforced with chitosan NPs. Moreover, Chen et al. (2022) [105] have investigated antibacterial nanofilm composites composed of gelatin from cold-water fish, chitosan, and ZnO. Notably, Arfat et al. (2017) [102] have meticulously prepared and examined the characteristics of antibacterial NC films originating from gelatin sourced from the bones of cold-water fish, combined with Silver–Copper (AgNPs and CuNPs). The efficacy of these NC films is evaluated against *L. monocytogenes*, *E. coli*, and *S. thyphimurium* and etc [17,89,102,103].

This evolving domain epitomizes the merging of innovative materials and advanced functionality. The amalgamation of fish gelatin with diverse additives to engender NCs with antimicrobial properties underscores the potential for these materials to revolutionize packaging and preservation techniques. The exploration of a wide array of composite formulations, the examination of their efficacy against specific bacterial strains, and the comprehensive assessment of their attributes collectively advance our comprehension of how biomaterial-based NCs can pave the way for enhanced food safety and preservation strategies. Table 3 presents nanofilm composite based on fish gelatin.

Based on this systematic review, we conclude that the potential applications of fish gelatin nanoparticles (NPs) encompass the food industry, pharmaceuticals, and biomedicine. In the food industry, fish gelatin NPs can serve as substitutes for conventional gelatin, acting as stabilizing or emulsifying agents based on nanoparticles. Several studies have demonstrated that nanostabilizers can prolong coalescence or aggregation, thereby enhancing emulsion stability [106]. Fish gelatin NC films can be utilized as food or edible packaging. The fabrication of NC films based on nanomaterials can enhance thermal, mechanical (ductility and tensile strength), and water barrier properties compared to conventional gelatin-based packaging [91,104]. Additionally, fish gelatin NC films can be employed as packaging for fruits or minimally processed foods such as meat and poultry, or other highly perishable food items, thus extending their shelf life. This review also found that NC films made from fish gelatin inhibit the growth of *Listeria monocytogenes* bacteria. *L. monocytogenes* is a pathogenic bacterium and a type of psychrophilic bacteria that can grow at cold temperatures, thus inhibiting the growth of this bacterium in minimally processed foods stored at cold temperatures. Many studies shown that by creating bulky material into NPs also enhance their antimicrobial properties [107].

The potential of fish gelatin NPs in the pharmaceutical industry lies

in their application as drug delivery systems, including oral delivery. Gelatin can be used as an encapsulant for both hydrophilic and hydrophobic bioactives. While conventional gelatin can also be used for drug delivery, utilizing its NP sizes can enhance solubility and increase the surface area of the delivery vehicles, thereby improving bioaccessibility and bioavailability, which impacts achieving adequate doses at target sites [46]. For instance, NP-enhanced bioavailability of drugs or bioactives occurs through their traversal across the gastrointestinal epithelium membrane following entry into the gastrointestinal tract via both non-intestinal epithelial routes (paracellular and M-cell pathways) and intestinal epithelial pathways [108]. Furthermore, in the biomedical industry or tissue engineering, converting fish gelatin into NPs or NFs (nanofibers) can enhance its adhesion and proliferation capabilities. Cell viability tests revealed that nanofibrous fish gelatin scaffolds exhibited good cell adhesion and proliferation rates compared to fish gelatin in film form. Furthermore, nanofibrous fish gelatin scaffolds demonstrate good cytocompatibility [96].

The transformation of conventional fish gelatin into fish gelatin nanoparticles/nanofibers/nanocomposites (NPs/NFs/NCs) represents a significant advancement in enhancing the adaptability of fish gelatin. The process of converting it into NPs/NFs/NCs not only amplifies its utility but also allows for the tailoring of its properties to meet specific demands across diverse industries such as food, pharmaceuticals, and biomedicine. This innovation ensures that products derived from fish gelatin NPs maintain key values including adherence to halal and kosher standards, utilization of natural ingredients, as well as considerations for sustainability, biodegradability, and environmental preservation. Consequently, consumers are offered products that align with their ethical and environmental preferences, reinforcing the appeal and versatility of fish gelatin in contemporary markets.

3.2. Fish gelatin NP and NF preparation

Several methods have been employed in the synthesis of fish gelatin NPs and NFs. The methodologies encompass desolvation [87,88,92,94], coacervation [98], electrospinning and crosslinking [90,96], as well as the Maillard reaction [95]. Each of these techniques offers distinct advantages and mechanisms for the creation of tailored NPs with specific attributes. All of these methods summarized in an illustration presented on Fig. 3.

Desolvation serves as a versatile approach, involving the precipitation of dissolved components through the controlled addition of non-solvent agents. Desolvation is a method frequently employed for generating NPs and microparticles (MPs) from dissolved materials. This technique operates on the principle of precipitating or aggregating soluble particles within a solution through the removal of the original solvent via the addition of a non-solvent or antisolvent. The desolvation process encompasses several stages, including solution preparation, solvent removal through antisolvent addition, agitation or mixing,

Table 3
Nanocomposite film based on fish gelatin as antimicrobial packaging.

Type of fish	Composite(s)	Technique for production	Antimicrobial activity	Ref.
Walleye pollock	ZnO/Chitosan	Solution casting method	<i>L. monocytogenes</i> , <i>S. aureus</i> , <i>E. coli</i> , <i>V. parahemolyticus</i>	[17]
Tilapia skin	ZnONPs + Ginger Oil	Emulsion casting method	<i>E. coli</i> & <i>L. monocytogenes</i>	[89]
Tilapia Skin	ZnO	Solution casting method	<i>Pseudomonas</i> , <i>Enterobacteriaceae</i>	[91]
Cold water fish	Chitosan + TPP	Solution casting method	<i>Staphylococcus aureus</i> , <i>Listeria monocytogenes</i> , <i>Salmonella enteritidis</i> and <i>Escherichia coli</i>	[97]
Not mentioned detail	ZnO nanorods	Solution casting method		[101]
Cold water fish skin	Silver–Copper NPs (AgNPs and CuNPs)	Solution casting method	<i>L. monocytogenes</i> , <i>E. coli</i> , <i>S. thyphimurium</i>	[102]
Tilapia Skin	Fish Protein Isolate + ZnO	Solution casting method	<i>Listeria monocytogenes</i> , <i>Pseudomonas aeruginosa</i>	[103]
Cold water fish skin	Chitosan + TPP	Solution casting method		[104]
Cold water fish skin	CM-Chitosan + ZnO	Solution casting method	<i>E. coli</i> and <i>S. aureus</i>	[105]

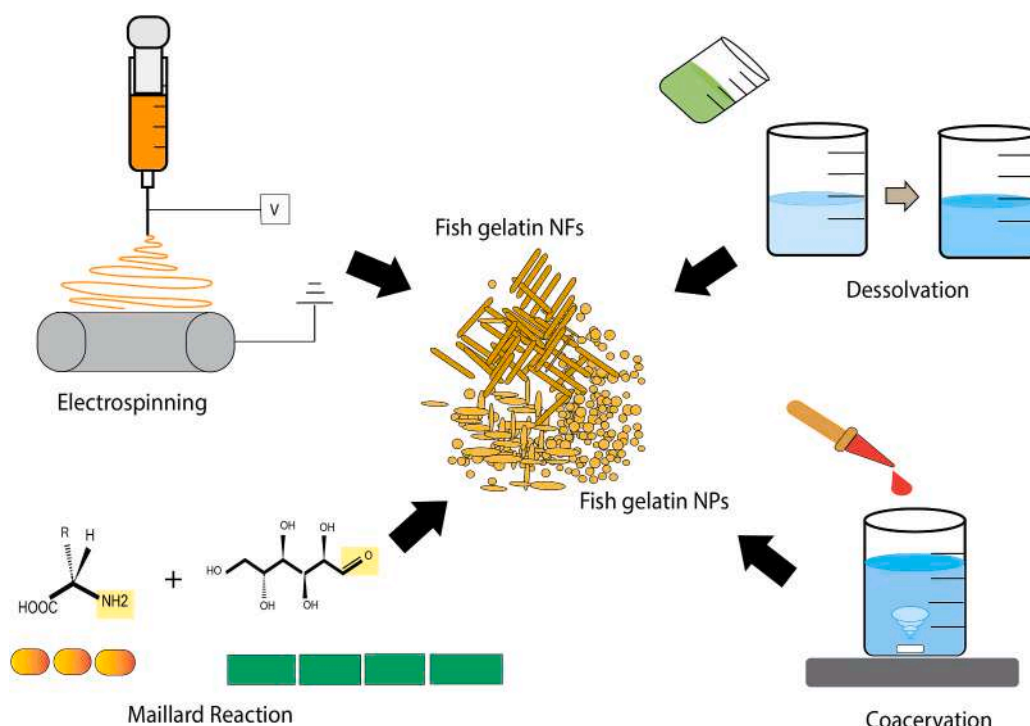


Fig. 3. Methods for synthesizing fish gelatin NPs or NFs.

particle formation, and eventual separation. Two distinct approaches have been undertaken in the production of fish gelatin NPs using the desolvation method: two-step desolvation [87,88,92] and one-step desolvation [94]. In the two-step desolvation, antisolvent is added twice, sequentially. The antisolvent may comprise acetone, ethanol, or isopropyl alcohol. Within the desolvation technique, a crosslinker agent such as glutaraldehyde is added during the particle formation stage prior to separation via centrifugation.

Coacervation involves the segregation of colloidal particles from a solution by inducing the formation of an additional liquid phase. The coacervation technique has also been explored in the production of fish gelatin hydrolysate hybrid NPs for use as biomaterials, as studied by Wu et al. (2015) [98]. In this investigation, coacervates were spontaneously generated upon the mixing of fish gelatin solution with tannic acid. Electrostatic interactions and hydrogen bonding were pivotal driving forces behind the creation of the colloidal NP suspension. This study exemplifies how the coacervation approach can be harnessed to engineer innovative biomaterials through careful manipulation of molecular interactions and phase separation dynamics.

The combination of electrospinning and crosslinking processes facilitates the creation of nanofiber (NF) structures or interconnected networks of NPs by harnessing electrostatic forces, followed by subsequent crosslinking to bolster stability. The underlying principle of electrospinning involves the utilization of an electric field to draw and elongate a charged polymer solution into delicate fibers, overcoming the inherent surface tension of the material. The application of the electric field induces the polymer solution to form a fine jet, which undergoes stretching and solidification as it advances toward a grounded collector, culminating in the production of NFs. Hani et al. (2016) [90] embarked on the production of NFs from gelatin sourced from the black Tilapia fish skin, with the intention of developing these NFs as delivery agents. The process entailed electrospinning fish gelatin NFs using varying concentrations, employing an experimental setup involving high voltage, a syringe pump, and a collector. Similarly, Kwak et al. (2017) [96] focused on generating gelatin NFs from cold-water fish for potential biomaterial applications. In their study, fish gelatin NFs were produced through the electrospinning method, employing distinct solvent systems—namely,

acetic acid/water and trifluoroethanol (TFE).

Conversely, the Maillard reaction exploits the intricate interplay between amino acids and reducing sugars, culminating in the creation of NPs endowed with multifaceted functional attributes. In the context of fish gelatin-chitooligosaccharide NPs, the synthesis process involves the preparation of a composite solution comprising gelatin and chitooligosaccharide at pH 6.0. This solution is subjected to incubation at a high temperature of 90 °C for a duration of 4 h, resulting in the formation of a composite product via the Maillard reaction. Subsequently, solutions containing apple polyphenols of varying concentrations are prepared independently. These solutions are then blended in diverse proportions, harnessing the potential of the Maillard reaction and composite formation. Through this methodological approach, the study delves into the characteristics of the resultant particles and investigates how these attributes evolve over time [95].

This investigative pursuit underscores the potential of the Maillard reaction to orchestrate intricate nanoscale interactions [95], thereby affording a mechanism to engineer NPs with tailored properties. The utilization of composite solutions and the manipulation of reaction parameters further emphasize the intricate control achievable within this methodology. By exploring the transformative journey of these particles and their dynamic attributes, this study extends our comprehension of the complex interplay between molecular constituents and reaction dynamics in the realm of nanoscale materials synthesis.

3.3. Fish gelatin nanofilm composite preparation

The synthesis of composite nanofilms based on fish gelatin has been conducted using two methods: the solution casting method [17,97,102,105] and the emulsion casting method [89]. In the solution casting method, fish gelatin is dissolved and heated to a specific temperature (45–70 °C), followed by the addition of a plasticizer such as glycerol. This mixture is then combined with a composite solution containing gelatin and other components like ZnO, Chitosan, Ag NPs, or Cu NPs, and homogenized. This stage yields a solution known as the film-forming suspension. Some studies incorporate a degasification step, which involves using a vacuum pump. The resulting film-forming

suspension is cast into a silicon resin plate or a rectangular plastic dish and allowed to dry at room temperature. The dried film is subsequently peeled from the mold or plate under controlled temperature and humidity conditions.

On the other hand, the emulsion casting method shares similarities with the solution casting method, but it involves the addition of an emulsified organic solution after mixing fish gelatin with the composite solution. This organic solution has been previously emulsified and is introduced at a specific stage [89].

Both methods exemplify the multifaceted approach to creating composite nanofilms from fish gelatin. The solution casting method showcases the sequential process of preparation, mixing, and casting, culminating in the formation of films with desired properties [17,91,97,102–105]. In comparison, the emulsion casting method introduces an additional layer of complexity by involving the incorporation of emulsified organic solutions into the process [89]. These methodologies contribute to the expanding repertoire of techniques for engineering nanoscale materials, leveraging the inherent properties of fish gelatin and other components to craft advanced composite films with tailored functionalities.

3.4. Characteristics of fish gelatin NPs, NFs, or NCs

3.4.1. Biophysical characteristics

Some characteristics need to be analyzed in the production of fish gelatin NPs. In this review, our focus centers on key attributes, namely size, polydispersity, surface charge, shape (morphology), and, notably, the interactions between fish gelatin and other constituents in the formation of composite nanofilms. Fig. 4 depicted approaches that have been used for characterization fish gelatin NPs, NCs or NFs.

The produced fish particles exhibit sizes within the nano and sub-micron range. The diameter ranges from approximately 40 nm–200 nm for fish gelatin NFs [90,96], while fish gelatin NPs vary between approximately 65 nm and 410 nm [88,92,95,98]. Based on the

conducted studies, we conclude that the incorporation of composites does not significantly influence the resulting NPs compared to single fish gelatin. Nonetheless, a more detailed analysis of this aspect is warranted. It is noteworthy that fish gelatin NFs from black Tilapia fish skin possess the smallest diameter [90]. The determination of particle diameters, both for fish gelatin NPs and NFs, is primarily achieved through dynamic light scattering (DLS) approach.

DLS, also known as Photon Correlation Spectroscopy (PCS), is a technique employed to measure the size distribution of particles, typically on the nano or micro scale, within a suspension or solution [109]. This method quantifies the movement of particles within a solution, often referred to as Brownian motion, and their interaction with light. The fluctuations of the scattered light resulting from particle motion are captured by a photodetector. Smaller particles exhibit faster fluctuations and consequently contribute to quicker signal fluctuations compared to larger particles [110,111]. The intensity of these fluctuations is then analyzed using a mathematical concept called the correlation function. The correlation function calculates the correlation between scattered light intensities at different time intervals, enabling the analysis of particle distribution and movement within a solution. Leveraging the Stokes-Einstein Equation and attributing particle movement within a solution to the diffusion coefficient, the hydrodynamic diameter can be determined. Furthermore, the width of the correlation function, referred to as "correlation decay," provides valuable insights into the distribution of particle sizes within the samples, denoted by the polydispersity index (PDI) [112]. A broader correlation decay signifies a higher PDI, indicative of a wider span of particle sizes [113]. A study undertaken by Khramtsov et al. (2021) [94] illustrated the PDI of fish gelatin NPs synthesized via one-step desolvation ranging from 0.014 to 0.127. Fish gelatin NPs synthesized using the two-step desolvation approach exhibited a PDI approximately ≤ 0.4 [87,88,92]. Meanwhile, the PDI of fish gelatin/chitosan-NPs produced through the Maillard reaction ranged from 0.165 to 0.496 [95]. Additionally, fish gelatin NC membranes derived from Tuna skin gelatin displayed pronounced

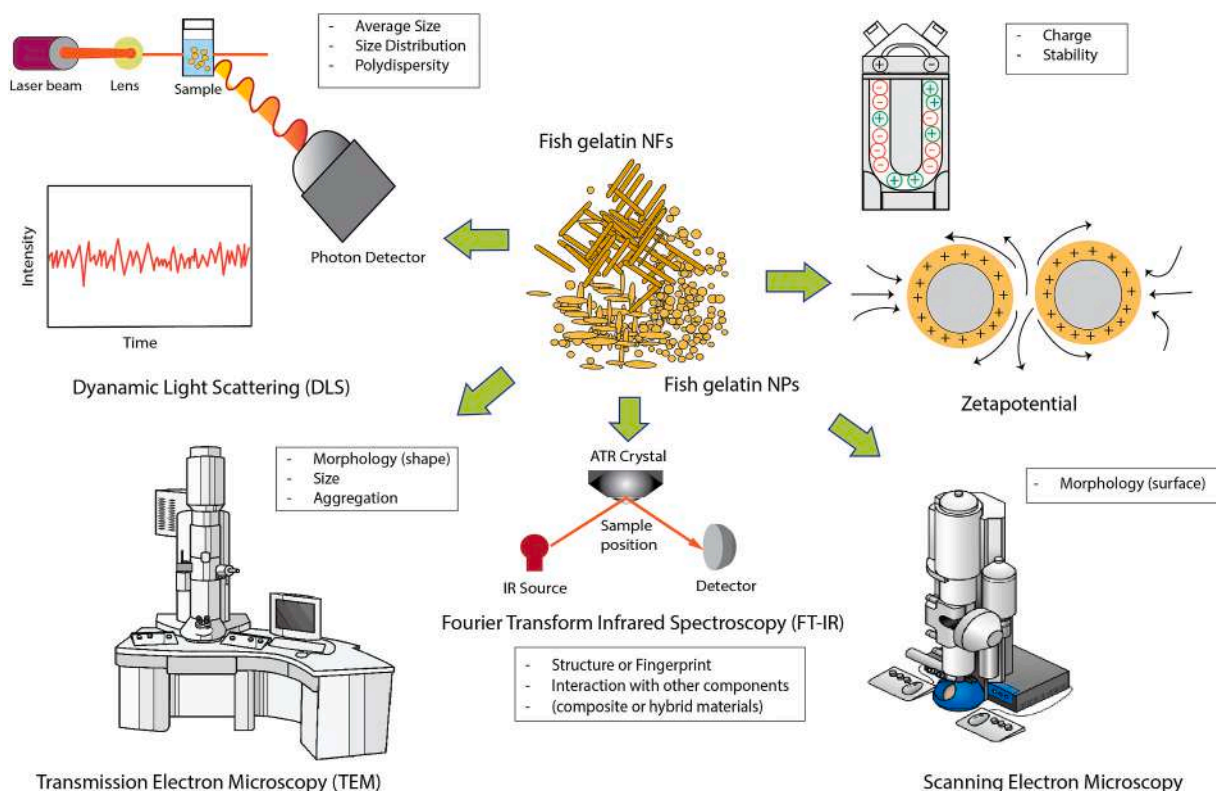


Fig. 4. Characterization of fish gelatin NPs and NCs.

polydispersity (PDI value was 0.535–0.890) [93].

Particularly, particles with a PDI of 0–0.1 are classified as monodisperse, signifying a high degree of uniformity [114]. Particles with a PDI falling within the range of 0.1–0.3 denote moderate polydispersity, indicating a relatively uniform distribution of sizes, albeit with a slightly broader size range compared to lower PDIs [115]. Within the moderate PDI range, most particles exhibit a similarity in size, although a small fraction may deviate in size either larger or smaller. Notably, a PDI range of 0.3–1.0 or >0.7 suggests a wide array of particle sizes within the samples, signifying a mixture containing significantly divergent particle sizes [116].

Stokes Einstein Eq (1):

$$D = \frac{KB T}{6 \pi \eta R}, dH = \frac{KB T}{6 \pi \eta D} \quad (1)$$

Where K_B is Boltzman's constant, T is temperature, η is viscosity and D is diffusion coefficient, dH is hydrodynamic radius [117]. And,

Correlation function (c) is defined by Eq (2):

$$C(\Delta t) = (I_s(t) \times I_s(t - \Delta t)) \quad (2)$$

where I_s is light intensity, and t is time [118].

As per the Stokes-Einstein Equation, it is widely acknowledged that maintaining controlled viscosity and temperature is of first importance in DLS-based size measurements [111]. Consequently, in the context of studies on fish gelatin NPs, the absence of detailed information regarding solution concentrations and viscosity levels results in size measurements being confined to estimations. Moreover, the NP diameter measurement technique using DLS presents several inherent limitations. For instance, accuracy diminishes when particles within a solution are excessively large, and as the method assumes the particles to be in a spherical form within the solution. It is also sensitive to the presence of particle aggregates in a solution, while occasionally failing to reflect the particle size in dry solid state [112]. Therefore, alternative techniques are employed to mitigate these shortcomings, such as scanning electron microscopy (SEM) and transmission electron microscopy (TEM), which will be elaborated upon subsequently.

The stability of fish gelatin NPs is assessed based on their zeta potential or electrokinetic potential values. The zeta potential values for fish gelatin NPs derived from Tilapia range from 21 ± 2.2 to 29 ± 1.6 mV [87], while those from Mirror carp fish skin measure between 18.1 and 19.8 mV [92]. In the study conducted by Wu et al. (2015) [98], fish gelatin hydrolyste hybrid NPs exhibited a zeta potential of 17.5 ± 0.5 to 22.7 ± 0.9 mV. Furthermore, fish gelatin/chitoooligo-NPs display a zeta potential of 21 ± 2.2 to 29 ± 1.6 mV [95]. The zeta potential is a crucial parameter for predicting colloidal stability, particle-particle interactions, and the charge of particles or colloids in a solution. A zeta potential of 0 mV is categorized as slight to no stability, ≤ 15 mV signifies less stability with slight settling, while ≥ 30 mV indicates moderate stability [119]. While zeta potential measurements are typically performed using the same instrument as the size distribution analysis, a dynamic light scattering (DLS) with a zetasizer, zeta potential measures the surface charge of colloidal particles using a separate technique known as "electrophoretic mobility" or "phase analysis light scattering (PALS)." In this method, an electric field is applied to the sample, and the velocity of charged particle movement in response to the electric field is measured [120,121]. Utilizing a folded cuvette with two poles, it is possible to determine how quickly particles in a solution move toward positive or negative poles. Zeta potential values are calculated based on electrophoretic mobility at 25 °C using the Smoluchowski equation in Eq (3) [122].

$$\zeta = \frac{4\pi\eta\mu}{\epsilon}, \text{ in which } \mu = \frac{\nu}{E} \quad (3)$$

Where ζ is zetapotential, η is viscosity buffer, μ is electrophoretic mobility, ϵ is the electric constant of the solvent, ν is velocity, and E is

electrical field [123].

Transmission electron microscopy (TEM) is a powerful imaging technique that enables scientists to observe the morphology (shape), size, and aggregation of nanomaterials at an exceptionally high resolution. In principle, when an electron beam strikes a sample in TEM, it undergoes interactions with the atoms within the sample. Those electrons that do not interact with the atoms are transmitted through the sample. These transmitted electrons then encounter an array of electromagnetic lenses collectively known as the objective lens system. These lenses serve to magnify the transmitted electrons and concentrate them into a focused, coherent beam. This focused electron beam subsequently impinges upon a fluorescent screen or digital camera, where the interactions between the electrons and the specimen led to variations in electron intensity. These variations combine to create an image characterized by exceptional spatial resolution [124–127].

Research conducted by Nuerjiang et al. (2023) [92] employed TEM to investigate fish gelatin NPs, revealing their spherical shape, monodispersity, and sizes corresponding to those measured using dynamic light scattering (DLS). This study concluded that an increase in glutaraldehyde concentration resulted in reduced NP aggregation. Conversely, fish gelatin NPs without glutaraldehyde or with fish gelatin-to-glutaraldehyde ratios of 12:1 or 12:2 led to the formation of NP aggregates. Similarly, Wu et al. (2015) [98] observed spherical fish gelatin NPs with sizes consistent with those determined by DLS analysis. An increase in tannic acid concentration, however, induced NP aggregations.

Scanning electron microscopy (SEM) has been used in the characterization of fish gelatin NPs, NFs, and NC films. Although SEM images may not precisely depict the actual size of NPs, this technique can excel in visually representing fish gelatin micro and nano-scale features, such as particles [94] or fibers [90,96]. Recent applications of SEM on fish gelatin NC have proven particularly valuable in assessing complexation between fish gelatin and its composites. For instance, in a study by Chen et al. (2022) [96], SEM analysis was employed to evaluate the incorporation of ZnO into the gel carboxymethyl cellulose (CMC) and fish gelatin matrix for composite nanofilms used in food packaging. The results demonstrate the compatibility between ZnO and CMC/fish gelatin. Furthermore, SEM has been utilized to analyze cross-sectional thickness and surface morphology, specifically smoothness and roughness, of composite nanofilms. For example, the CMC/fish gelatin/ZnO NC film exhibited uneven roughness and a fine pore structure [105]. The incorporation of fish gelatin NPs into collagen fibers resulted in a homogeneous, compact, flat, and smooth NC film [92]. Similarly, studies have shown that pristine fish gelatin possesses a smooth and homogeneous microstructure, with minimal changes observed when a small quantity of chitosan NPs is added. However, structural alterations become apparent with increased CsNP concentrations [97]. Arfat et al. (2017) [103] observed a similar phenomenon, where SEM images indicated that the smooth surface of neat fish gelatin film became rougher when combined with 2% Ag–Cu.

3.4.2. Functional properties of NCs based on fish gelatin

Characterization has been conducted on fish gelatin-based NC films, encompassing mechanical strength assessment as a pivotal component. The introduction of NPs in biopolymer film fabrication has been demonstrated to enhance tensile strength (TS) and Young's modulus (YM) [101,105]. This augmentation in the mechanical properties of composite films can be attributed to the robust intermolecular forces operating between carboxymethyl chitosan (CMCS) and gelatin. Notably, Rouhi et al. (2013) [101] observed that the incorporation of ZnO nanorods into gelatin films also led to a reduction in elongation at break (EAB). This phenomenon is intricately linked to moisture content and interfacial interactions between ZnO nanorods and the biopolymer matrix. Moreover, a reduced plasticizer content has been found to elevate TS and YM while diminishing EAB, owing to the pronounced mechanical interplay between the filler materials and the film matrix.

The incorporation of ZnO NPs into CMCS and gelatin composite films derived from cold fish skin has been instrumental in enhancing film plasticity and mechanical strength [105]. This improvement is underpinned by strong interactions between CMCS, gelatin, and ZnO NPs, closely related to their micron-scale structural characteristics, concurrently contributing to increased crystallinity [128].

Conversely, the utilization of Ag–Cu NPs at a concentration of 2% in gelatin films sourced from cold fish skin has been found to bolster TS while diminishing it at NP concentrations exceeding 2% [102]. The excessive loading of NPs beyond 2% impairs the film matrix's capacity to accommodate them, consequently undermining mechanical properties. EAB exhibited a declining trend with increasing NP concentration, attributed to heightened film rigidity. Notably, Ag–Cu NPs exhibit hydrophobic characteristics and tend to aggregate at specific concentrations, impeding protein domain organization and the amorphous network of gelatin films, thereby diminishing their mechanical attributes [102].

In summary, the characterization of fish gelatin-based NC films involves a comprehensive evaluation of their mechanical properties. The incorporation of NPs, such as ZnO and Ag–Cu, yields notable enhancements in TS and YM while influencing elongation at break. These improvements are ascribed to intricate intermolecular interactions, micron-scale structural features, and NP concentration effects, which collectively contribute to the overall mechanical performance of the films.

The introduction of chitosan NPs at an 8% concentration results in a noteworthy improvement in the TS of gelatin films derived from cold-water fish skin, enhancing it to 1.28 ± 1.02 MPa, compared to pure gelatin films devoid of chitosan NPs, which exhibited a TS of 7.44 ± 0.17 MPa [104]. The inclusion of chitosan NPs leads to the formation of more rigid films due to the reinforcing influence of these NPs within the polymer matrix. However, an inverse correlation is observed in the elongation at break (EAB), showing a diminishing trend with increasing CSNP content, declining from $102.04 \pm 28.38\%$ to $32.73 \pm 7.38\%$. This decline signifies an escalation in the brittleness of the fish gelatin film upon chitosan supplementation, primarily attributable to the reduction in free volume among polymer chains owing to heightened intermolecular attractive forces. Consequently, the polymer network becomes densely packed, rendering it less permeable. Furthermore, the elastic modulus (EM) of the gelatin film experiences a substantial increase of 60% with the augmentation of CSNP content, elevating it from 287.03 ± 14.25 to 467.2 ± 49.63 MPa. The EM value of the NC film from cold-water fish skin surpasses that of chitosan-containing gelatin films derived from fish bone, as reported by Jeya Shakila et al., in 2012, which stood at 378 MPa. This notable enhancement in elastic modulus holds considerable promise, particularly in the context of food packaging applications.

In addition, films fabricated from gelatin extracted from fish skin and fish protein isolates exhibit distinct characteristics under varying pH conditions. Alkaline pH conditions facilitate greater protein solubility, resulting in more substantial molecular stretching. Partial denaturation of myofibrillar proteins and the elongation of gelatin molecules ($\alpha 1$ and $\alpha 2$ chains) contribute to the formation of robust film networks characterized by high cross-linking densities. Films produced from gelatin extracted from fish skin and fish protein isolates, both with and without the incorporation of NP-ZnO, exhibit higher TS and lower EAB values when formulated under pH 11 conditions, in contrast to those produced at pH 3 [103]. The incorporation of NP-ZnO into films at pH 11 enhances the formation of salt bridges between Zn^{2+} ions and negatively charged residues, particularly COO[−] groups located on protein side chains or C-terminal. This phenomenon contributes to an increase in TS in the FPI/fish skin gelatin (FSG)-ZnO NC films. Notably, NPs possess high surface energy and a substantial specific surface area, fostering robust interfacial interactions between the polymer and NPs, thereby resulting in significant improvements in polymer properties [101,129].

3.4.3. Antimicrobial properties

The incorporation of essential oils has been shown to enhance antimicrobial activity in bio-composite films. Gelatin-based composite films derived from cold-water fish skin, combined with chitosan NPs, initially exhibit no significant antimicrobial activity against bacteria such as *S. aureus*, *L. monocytogenes*, *S. enteritidis*, and *E. coli*. However, upon the addition of oregano oil, these films manifest remarkable antimicrobial efficacy against all four bacterial strains [97]. A concentration of 1.2% (w/v) oregano oil effectively inhibits bacterial growth, yielding inhibition zones ranging from 26.3 to 33 mm. This antimicrobial activity is attributed to the presence of compounds such as carvacrol, thymol, and *p*-cymene [130]. Carvacrol and thymol can disrupt the outer membrane of gram-negative bacteria, leading to the release of vital cellular components [131], while *p*-cymene, a biological precursor of carvacrol, exhibits hydrophobic properties, causing the cytoplasmic membrane to expand more than carvacrol [132].

Furthermore, when meat is packaged using gelatin films derived from Tilapia fish skin, augmented with 3% NP ZnO (w/w, gelatine) and 80% ginger essential oil (GEO) (w/w, gelatine), a lower total bacterial count is observed compared to control films and films with varying concentrations (10%, 20%, and 40%) of ginger essential oil [89]. The total bacterial counts recorded are 4.6, 4.7, and 2.8 log colony forming unit per gram (CFU/g) for psychrotrophic, mesophilic, and lactic acid bacterial (LAB) groups, respectively. These counts are significantly lower ($P < 0.05$) than those found in control films and meat not packaged with the film. All tested samples exhibit bacterial counts below the threshold, except for films containing 10% GEO. The antimicrobial capability of essential oils, including ginger essential oil, is attributed to their ability to enhance cell membrane permeability and induce cytoplasmic leakage. Hydrophobic compounds within these oils can penetrate the double layers of phospholipids and interact with enzymes situated on the membrane [133]. Notably, at the same GEO concentration, gram-positive bacteria, like *L. monocytogenes*, are more susceptible than gram-negative bacteria such as *E. coli*. This discrepancy arises from the complex structure of gram-negative bacterial cell walls, which consist of a thin peptidoglycan layer, as opposed to the thick and multi-layered peptidoglycan structure of gram-positive bacteria [134]. Gram-negative bacteria are less sensitive due to the presence of an outer lipopolysaccharide membrane, which restricts the diffusion of hydrophobic agents in antibacterial substances. The outer membrane of gram-negative bacteria does not readily absorb Zn^{2+} ions released from ZnONPs and hydrocarbon cyclic hydroxyl groups in GEO compared to gram-positive bacteria [135]. Consequently, the inhibition of foodborne pathogenic microbes in FSG-ZnONP films is enhanced through the incorporation of GEO, especially against gram-positive bacteria.

The combination of gelatin and chitosan demonstrates the potential to inhibit the growth of microorganisms, thereby slowing down the spoilage process and extending shelf life, particularly at low temperatures. The addition of zinc oxide (ZnO) NPs at a 0.6% concentration to NC films derived from gelatin extracted from walleye pollock (*Theragra chalcogramma*) skin and chitosan significantly enhances inhibition zones against bacteria including *S. aureus*, *L. monocytogenes*, *E. coli*, and *V. parahaemolyticus*, measuring 8.50, 5.58, 7.91, and 6.97 mm, respectively. Gelatin/chitosan films containing ZnO exhibit substantially elevated antimicrobial activity, primarily due to photocatalysis processes and metal ion release [136]. The release of Zn^{2+} ions from ZnO NPs penetrates the microbial cell walls, impacting bacterial cell viability. ZnO is also known to mediate the production of hydrogen peroxide (H_2O_2), leading to membrane damage in bacterial cells [137]. This is further corroborated by research conducted by Arfat et al. (2016) [103], demonstrating that ZnO NPs incorporated into FPI/FSG films exhibit higher antibacterial activity against *L. monocytogenes* and *P. aeruginosa* compared to films lacking ZnO NPs.

Furthermore, composite films containing CMCS/Gelatin derived from cold-water fish skin and nano ZnO display greater antibacterial activity against *E. coli* compared to *S. aureus* (with antibacterial rates of

99.20% against *E. coli* and 84.70% against *S. aureus*) [105]. The variance in antibacterial efficacy is attributed to structural differences in the cell walls of these two bacterial strains. While the cell wall of gram-negative bacteria is complex, it consists of only a thin peptidoglycan layer. In contrast, gram-positive bacteria possess thick peptidoglycan layers with multiple levels [138]. When zinc ions released by nano zinc oxide traverse the cell layers, various reactive oxygen species are generated within the cell, resulting in cell death [139].

Lastly, composite films made from gelatin extracted from cold fish skin and incorporating Ag–Cu NPs at concentrations ranging from 1% to 4% demonstrate antibacterial activity against *L. monocytogenes* and *S. typhimurium*. The inhibitory mechanisms of Ag–Cu NPs against these bacteria involve the release of silver or copper ions, which can penetrate bacterial membrane pores and gaps, interact with disulfide or sulfhydryl enzyme groups, or adhere to negatively charged bacterial cell walls, disrupting metabolic processes, or causing bacterial cell wall rupture, ultimately leading to cell death [140].

It is generally accepted that converting into NP sizes enhancing antibacterial activity. A study conducted by Fu et al. (2021) [141] revealed the inhibitory effects of gelatin NPs derived from fish scales on the growth of *E. coli* and *S. aureus* bacteria. Nanocomposite films incorporating chitosan were found to offer robust protection and delay spoilage in fruits. This can be attributed to the antimicrobial properties of chitosan, which exhibit a broad-spectrum effect against both gram negative and gram positive bacteria as well as fungi.

Moreover, bio-nanocomposite films formulated with gelatin and chitosan enriched with carbon dots exhibited notable antibacterial activity against *E. coli* and *S. aureus*. While films containing gelatin and chitosan already demonstrated antibacterial efficacy against both bacterial strains, the addition of carbon dots to the gelatin/chitosan film resulted in a significant increase in inhibitory zones [141]. This enhancement can be attributed to the positively charged amino groups within the carbon dots, which interact with negatively charged macromolecules on the bacterial cell surface. Additionally, the positively charged nature of carbon dots contributes to their inherent antibacterial properties. Consequently, the combined presence of chitosan and carbon dots led to higher antibacterial activity in the gelatin/chitosan/carbon dots film compared to the gelatin/chitosan film [141].

4. Prospects and techniques for developing nanomaterials enhancements from pangasius catfish

As far as our current knowledge extends, there have been no published research findings specifically concerning fish gelatin NPs, NFs, or composites derived from *Pangasius catfish*/Patin. However, if gelatin from other fish, especially those from warm-water species like *Tilapia* [87,88,90] and *Tuna* [93], can be developed into nanomaterials, it is reasonable to assume that *Pangasius catfish* gelatin can be developed as well. The process of developing *Pangasius catfish* gelatin into NPs can follow similar techniques used in the development of gelatin NPs from *Tilapia* fish skin, such as the two-step desolvation method [87,88,92], or into NFs using electrospinning [90,96]. Furthermore, *Pangasius catfish* gelatin can also be employed as a constituent in nanofilm composites alongside ZnO [17,91,105]. Nevertheless, optimization of the fabrication process and characterization of the final products are essential to compare them with NPs from other fish sources or from commercial products.

Actually, more than a decade ago, techniques for producing gelatin NPs from mammalian gelatin were already studied, but these techniques have not yet been applied to fish gelatin. These techniques include emulsification-solvent evaporation [142,143], reverse phase micro-emulsion [144], nanoprecipitation [145,146], and self-assembly [147,

148]. Fig. 5 shows other techniques that potentially can be adopted to produce fish gelatin NPs.

The emulsification-solvent evaporation technique is based on a single water-in-oil (W/O) emulsion, where the aqueous phase containing gelatin is added dropwise into the organic phase while stirring. This process forms an emulsion, which is then cooled to around 5 °C to promote NP formation, followed by crosslinking. In this technique, if the NPs are used as a delivery vehicle, the bioactive compound is initially dissolved depending on its solubility. If the bioactive compound is soluble in water, it is dissolved along with the gelatin solution in the aqueous phase. However, if it is soluble in organic solvents, it is mixed and dissolved in the organic phase first [142,143,149,150].

Gelatin NPs can also be synthesized using the reverse phase micro-emulsion technique. In this method, the gelatin solution is poured into the organic phase containing a surfactant, followed by the addition of a crosslinker. The crosslinker acts within the core or internal emulsion (W/O emulsion). The surfactant stabilizes the emulsion by providing its hydrophobic tail to the external part, interacting with the organic phase, while its hydrophilic head interacts with the gelatin in the internal/aqueous phase. Subsequently, evaporation is carried out to remove the organic solvent phase [144,149–151].

Another technique is nanoprecipitation, where the gelatin in the aqueous phase is added slowly into ethanol, which serves as the non-solvent phase containing a crosslinker and stabilizer. The mixing process induces interface turbulence due to limited mixing ability, and as turbulent mixing continues, tiny droplets are formed on the nanoscale, called "nanodroplets." These nanodroplets are inherently unstable due to the immiscibility of the two liquids, but the stabilizer prevents them from separating. Over time, the solvent gradually diffuses and spreads into the surrounding liquid, leaving solid particles suspended in a solution [145,146,149–151].

The last technique that can be used to produce fish gelatin NPs is self-assembly. Self-assembly can be utilized to create gelatin NPs for encapsulating bioactive compounds without external process intervention. Essentially, NPs are formed due to hydrogen bonding and hydrophobic interactions either among gelatin structures or with bioactive compounds. Gelatin is a protein with a relatively high content of hydrophobic amino acids such as proline, hydroxyproline, leucine, isoleucine and phenylalanine. The protein structure can be loose and extended in a random coil conformation, and importantly, it has numerous sites on its surface for interacting with other molecules [147, 148,150].

In light of the extensive studies conducted on gelatin and fish gelatin NPs, it is evident that a meticulous optimization process is essential to establish a robust protocol for the production and advancement of fish NPs derived from Patin fish gelatin. This optimization entails a comprehensive series of key stages. Firstly, the selection of an appropriate gelatin extraction methodology from Patin fish waste forms the foundational step. Subsequently, the characterization of the extracted liquid gelatin is imperative for understanding its properties and quality. Following this, the synthesis of gelatin NPs demands the application of techniques tailored to the desired product specifications. These may include the development of pure gelatin-based particles, fibers, or the creation of hybrid and composite fish nanogelatin structures. The fourth stage necessitates the comprehensive characterization of the produced gelatin NPs, NFs, or other nanoproducts to ensure their conformity with predetermined criteria. The ensuing stages encompass the isolation, thorough washing, and purification of these products, culminating in the sixth stage, which involves the drying process. The dried product is then subjected to a detailed characterization in the seventh stage. Finally, the protocol must encompass stability testing throughout storage, accompanied by a rigorous specification analysis. This multifaceted approach

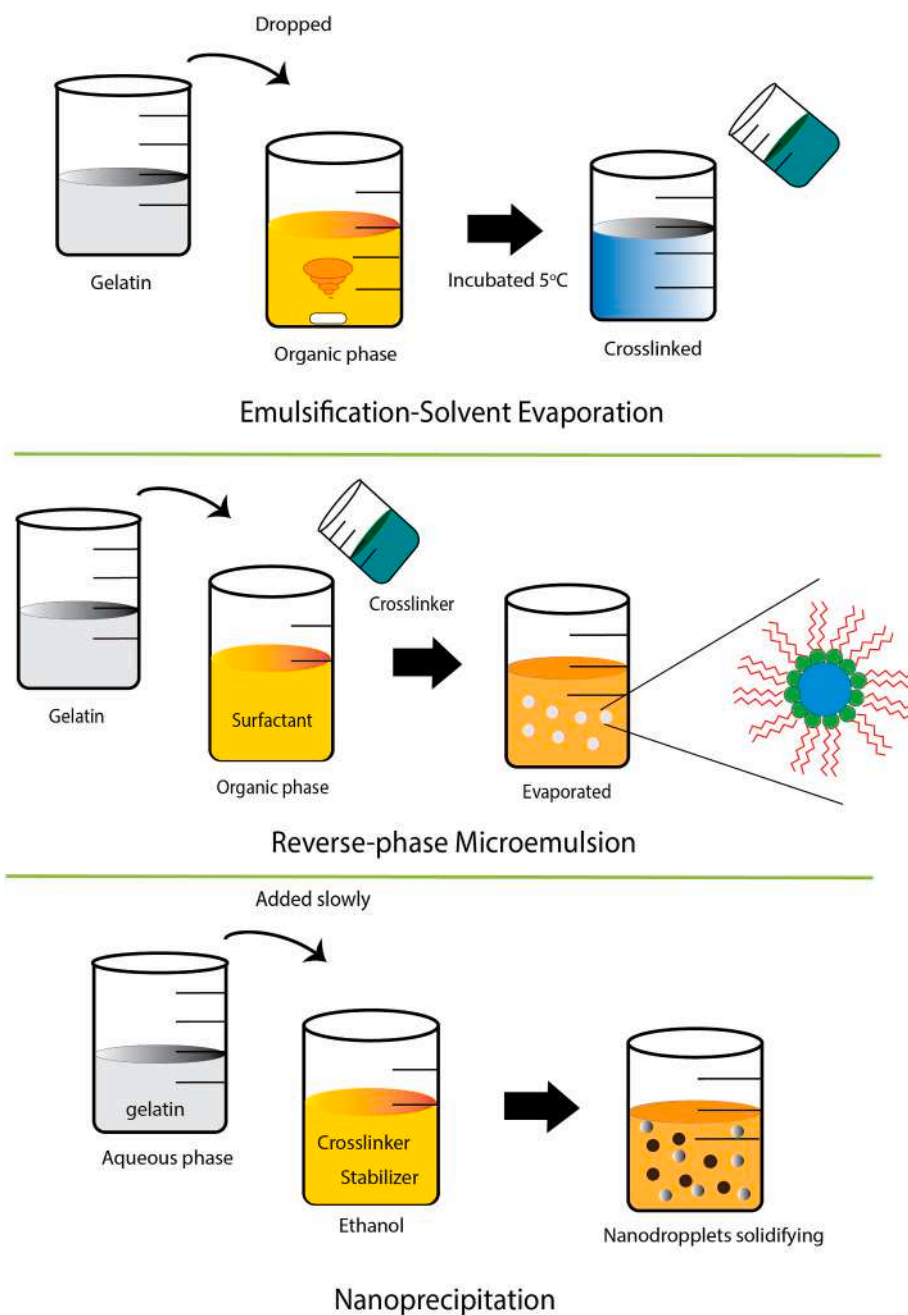


Fig. 5. Another option techniques for synthesis fish gelatin NPs.

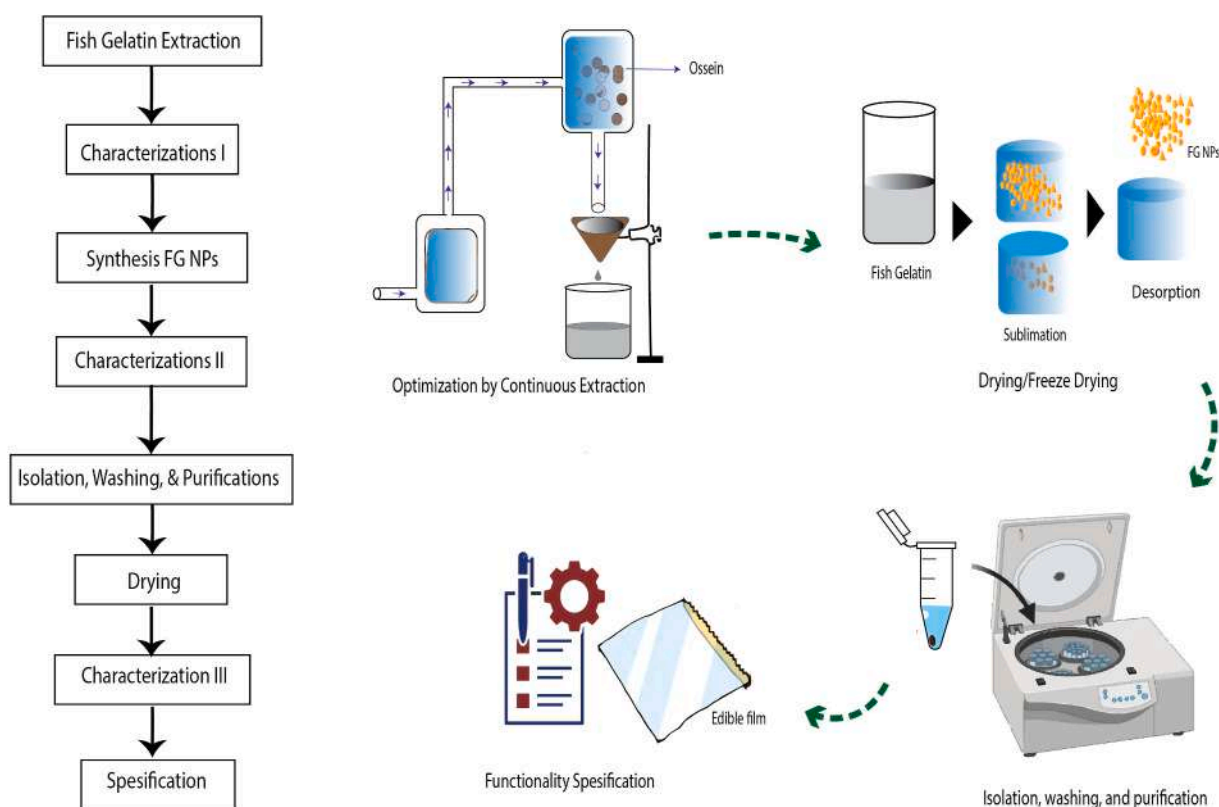


Fig. 6. Flow chart steps and an exemplification for FG NPs development from downstream to upstream.

ensures the systematic development of Patin fish gelatin-based NPs, fostering a robust foundation for future research and industrial applications. Fig. 6 presenting steps that potentially enable to follow in order to develop fish gelatin NPs.

5. Challenge and opportunities on NPs and NC from *Pangasius* sp. gelatin

The endeavor to develop fish gelatin and fish gelatin NPs from *Pangasius* catfish into nanomaterials presents an intriguing avenue of research, accompanied by a host of formidable challenges. As of now, no definitive formula has emerged to address these multifaceted issues. These challenges encompass the low extraction yield of gelatin from raw materials [14,57,63,80], the inherent weakness of fish gelatin in terms of gel strength [79], prevalent usage of organic solvents [54,67] and crosslinking agents in the synthesis processes [97,104], and the complex regulatory landscape surrounding the commercialization of nanomaterials worldwide like in the European which also implicate to Indonesia [152,153]. In this section, each of these challenges is elucidated in detail, with an exploration of potential opportunities and solutions that merit pursuit.

Low extraction yield of gelatin from raw materials. The primary challenge encountered in this pursuit is the modest extraction yield of gelatin from raw materials [14,57]. Specifically, the process of converting raw materials into gelatin yields less than optimal results. While data related to the yield of NPs from fish gelatin remains scarce, it is reasonable to infer that the yield is even lower. To address this, it is imperative to secure a consistent and ample supply of raw *Pangasius* catfish gelatin material. This necessitates a meticulous approach to optimizing the production of *Pangasius* catfish gelatin, leveraging statistical methodologies such as response surface methodology (RSM) to ascertain the ideal conditions for pre-treatment and main extraction [67,85,154]. Notably, a shift from traditional batch extraction methods to continuous extraction techniques could hold the potential for yield enhancement

[155]. Additionally, under the conventional batch extraction approach, ossein byproduct, which constitutes a substantial portion of the initial raw material weight, is often underutilized. Implementing strategies to re-extract ossein could bolster gelatin yield significantly.

Weak gel strength of fish gelatin. Another critical challenge lies in the inferior gel strength of fish gelatin relative to its mammalian counterparts, thereby limiting its suitability for applications requiring robust film-forming capabilities. This limitation can be overcome through judicious blending of fish gelatin with compatible materials, as demonstrated in previous studies on fish gelatin NCs. Furthermore, the augmentation of fish gelatin with other polymer substances presents a viable strategy to bolster its gel strength, particularly in contexts such as biomaterials or coatings. Promising candidates for such blending include alginate [156,157], chitosan [158,159], or other proteinaceous materials [160,161]. Moreover, the illustrative examples are in the review conducted by Atma (2022) [162], which present synthesized a hybrid fish gelatin-composite, resulting in improved gel strength while concurrently embracing principles of sustainability and safety.

Utilization of organic solvents and crosslinker agents. The third critical challenge revolves around the prevalent utilization of organic solvents and crosslinking agents in the process of synthesizing fish gelatin NPs. This practice, while effective, introduces concerns related to biocompatibility, given the inherent toxicity of such agents. To circumvent this challenge, a pivotal strategy is the adoption of more environmentally sustainable nanogelatin production techniques that circumvent the need for organic solvents. Such techniques may involve coacervation [98, 150] or self-assembly processes [147,148,150] devoid of crosslinking agents. Alternatively, crosslinkers may be replaced with naturally occurring polymers possessing counteractive charge properties relative to fish gelatin. In practice, crosslinkers primarily serve to facilitate interactions between gelatin and composite materials or gelatin clusters. Recent studies have successfully forged polyelectrolyte complexes by harnessing ionic interactions between gelatin and naturally charged biopolymers. These interactions, synergizing with hydrogen bonding

and hydrophobic forces, impart robust binding capabilities between gelatin and its biopolymeric counterparts [163,164]. This approach also absolutely categorized as green nanotechnology for sustainable environment [110,165].

Regulatory complexities. The final challenge pertains to the intricate regulatory landscape governing the commercialization of nanomaterials in Indonesia. These regulations present a formidable hurdle to the development and application of nanomaterials. For instance, nano-sized components within products, including proteins such as gelatin, are subject to stringent non-food materials legislation in certain regions, posing substantial compliance and investment challenges for both laboratory research and industrial-scale production [166,167]. In light of these regulatory nuances, customizing or formulating fish gelatin to achieve specific size ranges, such as the submicron (100–1000 nm) scale, emerges as a pragmatic approach [168]. Within this submicron range, fish gelatin can be managed akin to conventional components or ingredients, aligning seamlessly with established food regulations and circumventing potential regulatory bottlenecks.

In conclusion, the development of fish gelatin and fish gelatin NPs from *Pangasius catfish* into nanomaterials is an intricate pursuit marked by multifaceted challenges. These challenges, ranging from suboptimal extraction yields to gel strength limitations, reliance on toxic synthesis processes, and intricate regulatory frameworks, necessitate a comprehensive and innovative approach. Addressing these challenges holds the potential to unlock the vast possibilities of fish gelatin and its NPs in various scientific and industrial applications, ultimately enriching both the scientific discourse and industrial landscape.

CRediT authorship contribution statement

Yoni Atma: Conceptualization, Visualization, Writing – original draft, Writing – review & editing. **Nina Jusnita:** Investigation, Writing – review & editing, Writing – original draft. **Susiana Melanie:** Writing – review & editing. **Moh Taufik:** Investigation, Writing – review & editing. **Muhammad Yusuf:** Conceptualization, Writing – review & editing.

Declaration of competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

No data was used for the research described in the article.

Acknowledgement

The authors are grateful to the following institutions: Center for Higher Education Funding (BPPT), the Ministry of Education, Culture, Research and Technology of the Republic of Indonesia, and Indonesian Endowment Fund for Education (LPDP) for PhD study of Yoni Atma, Nina Jusnita, and Susiana Melanie.

References

- [1] GME, Standardised methods for the testing of edible gelatine, in: Gelatine Monograph, 2020.
- [2] UNComtrade, Trade data, UN comtrade. <https://comtradeplus.un.org/TradeFlow>, 2020.
- [3] Z. Zilhadia, Y. Harahap, I. Jaswir, E. Anwar, Evaluation and characterization of hard-shell capsules formulated by using goatskin gelatin, *Polymers* 14 (2022) 1–13, <https://doi.org/10.3390/polym14204416>.
- [4] S. Nitsuwat, P. Zhang, K. Ng, Z. Fang, Fish gelatin as an alternative to mammalian gelatin for food industry: a meta-analysis, *Lwt* 141 (2021) 110899, <https://doi.org/10.1016/j.lwt.2021.110899>.
- [5] G. Boran, J.M. Regenstein, *Fish Gelatin*, first ed., Elsevier Inc., 2010 [https://doi.org/10.1016/S1043-4526\(10\)60005-8](https://doi.org/10.1016/S1043-4526(10)60005-8).
- [6] M.C. Gómez-Guillén, M. Pérez-Mateos, J. Gómez-Estaca, E. López-Caballero, B. Giménez, P. Montero, Fish gelatin: a renewable material for developing active biodegradable films, *Trends Food Sci. Technol.* 20 (2009) 3–16, <https://doi.org/10.1016/j.tifs.2008.10.002>.
- [7] A.A. Karim, R. Bhat, Fish gelatin: properties, challenges, and prospects as an alternative to mammalian gelatins, *Food Hydrocolloids* 23 (2009) 563–576, <https://doi.org/10.1016/j.foodhyd.2008.07.002>.
- [8] R.L. Olsen, J. Toppe, I. Karunasagar, Challenges and realistic opportunities in the use of by-products from processing of fish and shellfish, *Trends Food Sci. Technol.* 36 (2014) 144–151, <https://doi.org/10.1016/j.tifs.2014.01.007>.
- [9] J.C. Zamorano-Apodaca, C.O. García-Sifuentes, E. Carvajal-Millán, B. Vallejo-Galland, S.M. Scheuren-Acevedo, M.E. Lugo-Sánchez, Biological and functional properties of peptide fractions obtained from collagen hydrolysate derived from mixed by-products of different fish species, *Food Chem.* 331 (2020) 127350, <https://doi.org/10.1016/j.foodchem.2020.127350>.
- [10] C.G. Sotelo, M.B. Comesaña, P.R. Ariza, R.I. Pérez-Martín, Characterization of collagen from different discarded fish species of the west coast of the Iberian Peninsula, *J. Aquat. Food Prod. Technol.* 25 (2016) 388–399, <https://doi.org/10.1080/10498850.2013.865283>.
- [11] P.D. Karayannakidis, A. Zotos, Fish processing by-products as a potential source of gelatin: a review, *J. Aquat. Food Prod. Technol.* 25 (2016) 65–92, <https://doi.org/10.1080/10498850.2013.827767>.
- [12] BPS, Produksi perikanan tangkap di Laut menurut komoditas utama (ton), 2019–2021, Badan Pus. Stat., 2021. <https://www.bps.go.id/indicator/56/1515/1/produksi-perikanan-tangkap-di-laut-menurut-komoditas-utama.html>.
- [13] Kkp, Produksi Perikanan, Kementerian, Perikan. Dan Kelaut, 2022. https://statistik.kkp.go.id/home.php?m=prod_ikan_prov&i=2.
- [14] Y. Atma, H. Ramdhani, Gelatin extraction from the indigenous *Pangasius catfish* bone using pineapple liquid waste, *Indones. J. Biotechnol.* 22 (2018) 86, <https://doi.org/10.22146/ijbiotech.32472>.
- [15] J.H. Muyonga, C.G.B. Cole, K.G. Duodu, Characterisation of acid soluble collagen from skins of young and adult Nile perch (*Lates niloticus*), *Food Chem.* 85 (2004) 81–89, <https://doi.org/10.1016/j.foodchem.2003.06.006>.
- [16] M.V. Chandra, B.A. Shamasundar, Rheological properties of gelatin prepared from the swim bladders of freshwater fish Catla catla, *Food Hydrocolloids* 48 (2015) 47–54, <https://doi.org/10.1016/j.foodhyd.2015.01.022>.
- [17] Z. Liu, M. Lv, F. Li, M. Zeng, Development, characterization, and antimicrobial activity of gelatin/chitosan/ZnO nanoparticle composite films, *J. Aquat. Food Prod. Technol.* 25 (2016) 1056–1063, <https://doi.org/10.1080/10498850.2014.923081>.
- [18] K. Jellouli, R. Balti, A. Bougateg, N. Hmidet, A. Barkia, M. Nasri, Chemical composition and characteristics of skin gelatin from grey triggerfish (*Balistes capricornus*), *Lwt* 44 (2011) 1965–1970, <https://doi.org/10.1016/j.lwt.2011.05.005>.
- [19] Kominfo, Industri Patin Indonesia rebut pasar global, Kemneterian Komun. Dan Inform (2018). https://www.kominfo.go.id/content/detail/12874/industri-patin-indonesia-rebut-pasar-global/0/artikel_gpr.
- [20] IndonesiaBaik, Sentra produksi Patin Indonesia, Indones. Baik, <https://indonesiabaik.id/infografis/sentra-produksi-patin-indonesia>, 2015.
- [21] A.R. Sefrienda Jasmadi, B. Kumayanjati, D.E.D. Setyono, H. Herdian, H. Novianty, Effects of physical treatments on size particle and nutritional properties of bone powder from *Pangasius* sp., *IOP Conf. Ser. Earth Environ. Sci.* 1119 (2022), <https://doi.org/10.1088/1755-1315/1119/1/012037>.
- [22] Y.P. Khor, S.Y. Wan, C.P. Tan, G. Zhao, C. Li, Y. Wang, Y. Li, Potential of using basa catfish oil as a promising alternative deep-frying medium: a thermo-oxidative stability study, *Food Res. Int.* 141 (2021) 109897, <https://doi.org/10.1016/j.foodres.2020.109897>.
- [23] B.M. Rao, L.N. Murthy, M.M. Prasad, DBT-Bacteriophages project view project shelf life of chill stored pangasius (*Pangasianodon hypophthalmus*) fish filets: effect of vacuum and polyphosphate, *Artic. Indian J. Fish.* 60 (2013) 93–98. <https://www.researchgate.net/publication/295602598>.
- [24] N.B. Rathod, A.U. Pagarkar, K.H. Pujari, P.E. Shingare, S.B. Satam, G.G. Phadke, B.V. Gaikwad, Status of valuable components from pangasius: a review, *Int. J. Curr. Microbiol. Appl. Sci.* 7 (2018) 2106–2120, <https://doi.org/10.20546/ijcmas.2018.704.241>.
- [25] D. Wang, Y.H.P. Hsieh, The use of imported pangasius fish in local restaurants, *Food Control* 65 (2016) 136–142, <https://doi.org/10.1016/j.foodcont.2016.01.016>.
- [26] R.A. Abd El-Fatah, M.A. Rozan, H.M. Ziena, K. Imre, A. Morar, V. Herman, H.H. S. Abdel-Naeem, Improvement of microbial quality, physicochemical properties, fatty acids profile, and shelf life of basa (*Pangasius bocourti*) filets during chilling storage using pepsin, rosemary oil, and citric acid, *Foods* 12 (2023), <https://doi.org/10.3390/foods12224170>.
- [27] T.X. Le Thi, H.L. Tran, T.S. Cu, S.L. Ho, Separation and enrichment of Omega 3, 6, and 9 fatty acids from the by-products of vietnamese basa fish processing using deep eutectic solvent, *J. Chem.* 2018 (2018), <https://doi.org/10.1155/2018/6276832>.
- [28] T.X. Le Thi, Survey composition and content of omega-3,6,9, extracted from catfish at Mekong delta Vietnam by extraction method with the traditional solvents, *Vietnam J. Chem.* 55 (2017) 551–556.
- [29] A. Debbarma, V. Kumar, P.K. Mishra, A.S. Kakatkar, R.K. Gautam, F. Umra, S. Chatterjee, Valorisation of Basa fish (*Pangasius bocourti*) waste: oil extraction and encapsulation, *Int. J. Food Sci. Technol.* 58 (2023) 2764–2771, <https://doi.org/10.1111/ijfs.16117>.
- [30] L.C. Barman, M.B.H. Sikder, I. Ahmad, J.H. Shouroufe, S. Samiur Rashid, A.N. M. Ramli, Gelatin extraction from the Bangladeshi pangas catfish (*Pangasius*

- pangasius*) waste and comparative study of their physicochemical properties with a commercial gelatin, *Int. J. Eng. Technol. Sci.* 7 (2021) 13–23, [10.15282/ijets.7.2.2020.1002](https://doi.org/10.15282/ijets.7.2.2020.1002).
- [31] T. Prommajak, P. Raviyan, Physical properties of gelatin extracted from skin of Thai panga fish (*Pangasius bocourti* Sauvage), *Food Appl. Biosci. J.* 1 (2013) 131–145, https://www.agro.cmu.ac.th/fabjournal/data/2013_V1/12_FABJ1_3_2013.pdf.
 - [32] Pasar Kompas, Patin Potensial, Tetapi industrinya masih tertinggal, Kompas, <https://www.kompas.id/baca/ekonomi/2023/04/19/pasar-patin-potensial-tetapi-industrinya-masih-tertinggal>, 2021.
 - [33] O.V. Mikhailov, Gelatin as it is: history and modernity, *Int. J. Mol. Sci.* 24 (2023), <https://doi.org/10.3390/ijms24043583>.
 - [34] Y. Ding, Q. Wang, G. Zhu, P. Zhang, Y. Rui, Application and perspectives of nanopesticides in agriculture, *J. Nanoparticle Res.* 25 (2023) 1–15, <https://doi.org/10.1007/s11051-023-05811-5>.
 - [35] R.A.G. Hes, J.D. Painter, G.J. Appleby-Thomas, Optimal skin simulant for ballistic testing, *Forensic Sci. Int.* 346 (2023) 111653, <https://doi.org/10.1016/j.forsciint.2023.111653>.
 - [36] E. Mauri, S. Scialla, Nanogels based on hyaluronic acid as potential active carriers for dermatological and cosmetic applications, *Cosmetics* 10 (2023) 1–19, <https://doi.org/10.3390/cosmetics10040113>.
 - [37] S. Kour, N. Sharma, N. Balaji, P. Kumar, J.S. Soodan, M.V. dos Santos, Y.O. Son, Advances in Diagnostic Approaches and Therapeutic Management in Bovine Mastitis, 2023, <https://doi.org/10.3390/vetsci10070449>.
 - [38] M. Oh, W. Shin, D. Kim, J. Kim, I. Kim, H. Ju Choi, K. Chung, S. Lee, Temperature-directed fluorescent switchable nanoparticles based on P3OT-PNIPAM nanogel composite, *Eur. Polym. J.* 196 (2023), <https://doi.org/10.1016/j.eurpolymj.2023.112331>.
 - [39] N. Nassar, S. Kasapis, Fundamental advances in hydrogels for the development of the next generation of smart delivery systems as biopharmaceuticals, *Int. J. Pharm.* 633 (2023) 122634, <https://doi.org/10.1016/j.ijpharm.2023.122634>.
 - [40] F. Milano, A. Masi, M. Madaghiele, A. Sannino, L. Salvatore, N. Gallo, Current trends in gelatin-based drug delivery systems, *Pharmaceutics* 15 (2023), <https://doi.org/10.3390/pharmaceutics15051499>.
 - [41] C.R. Huang, C.H. Chang, Y.C. Su, T.J. Tseng, Y.F. Chen, Organic disulfide crosslinked nucleic acid-based nanocarriers for anticancer drug applications, *J. Drug Deliv. Sci. Technol.* 86 (2023) 104643, <https://doi.org/10.1016/j.jddst.2023.104643>.
 - [42] Y. Lou, T. Jiang, J. Yi, X. Ren, X. Wang, D. Fan, H. Ma, Q. Wei, Biocompatible protein nanogels as robust signal labels for persistent chemiluminescence immunoassays, *Colloids Surfaces A Physicochem. Eng. Asp.* 676 (2023) 132181, <https://doi.org/10.1016/j.colsurfa.2023.132181>.
 - [43] A. Sadeghi, S. PourEskandar, E. Askari, M. Akbari, Polymeric nanoparticles and nanogels: how do they interact with proteins? *Gels* 9 (2023) <https://doi.org/10.3390/gels9080632>.
 - [44] M. He, M. Zhang, T. Gao, Z. Liu, L. Chen, Y. Liu, Y. Huang, F. Teng, Y. Li, Fabrication and characterization of succinylated and glycosylated soy protein isolate and its self-assembled nanogel, *Int. J. Biol. Macromol.* 244 (2023) 125104, <https://doi.org/10.1016/j.ijbiomac.2023.125104>.
 - [45] C. Wu, Z. Zhi, M. Duan, J. Sun, H. Jiang, J. Pang, Insights into the formation of carboxymethyl chitosan-nisin nanogels for sustainable antibacterial activity, *Food Chem.* 402 (2023) 134260, <https://doi.org/10.1016/j.foodchem.2022.134260>.
 - [46] Y. Tan, Y. Zi, J. Peng, C. Shi, Y. Zheng, J. Zhong, Gelatin as a bioactive nanodelivery system for functional food applications, *Food Chem.* 423 (2023), <https://doi.org/10.1016/j.foodchem.2023.136265>.
 - [47] H. Tang, S. Yang, J. Chang, X. Zhao, J. Huang, G. Yu, Y. Feng, X. Zhou, J. Li, Interfacial characterization of an oxidative pickering emulsion stabilized by polysaccharides/polyphenol complex nanogels via a multiscale study, *Colloids Surfaces A Physicochem. Eng. Asp.* 660 (2023) 130791, <https://doi.org/10.1016/j.colsurfa.2022.130791>.
 - [48] A. Labanni, M. Nasir, S. Arief, Research progress and prospect of copper oxide nanoparticles with controllable nanostructure, morphology, and function via green synthesis, *Mater. Today Sustain.* (2023) 100526, <https://doi.org/10.1016/j.mtsust.2023.100526>.
 - [49] A. Hussain, M.N. Lakhan, A. Hanan, I.A. Soomro, M. Ahmed, F. Bibi, I. Zehra, Recent progress on green synthesis of selenium nanoparticles – a review, *Mater. Today Sustain.* 23 (2023) 100420, <https://doi.org/10.1016/j.mtsust.2023.100420>.
 - [50] V.D. Sharma, V. Vishal, G. Chandan, A. Bhatia, S. Chakrabarti, M.K. Bera, Green, sustainable, and economical synthesis of fluorescent nitrogen-doped carbon quantum dots for applications in optical displays and light-emitting diodes, *Mater. Today Sustain.* 19 (2022) 100184, <https://doi.org/10.1016/j.mtsust.2022.100184>.
 - [51] M.A. Sántiz-Gómez, M.A. Mazorra-Manzano, H.E. Ramírez-Guerra, S. M. Scheuren-Acevedo, G. Navarro-García, R. Pacheco-Aguilar, J.C. Ramírez-Suárez, Effect of acid treatment on extraction yield and gel strength of gelatin from whiptail stingray (*Dasyatis brevis*) skin, *Food Sci. Biotechnol.* 28 (2019) 751–757, <https://doi.org/10.1007/s10068-018-0514-y>.
 - [52] V. Venupriya, V. Krishnaveni, M. Ramya, Effect of Acidic and Alkaline Pretreatment on Functional, Structural and Thermal Properties of Gelatin from Waste Fish Scales, Springer Berlin Heidelberg, 2023, <https://doi.org/10.1007/s00289-022-04600-9>.
 - [53] F. Mahmoodani, V.S. Ardekani, S.F. See, S.M. Yusop, A.S. Babji, Optimization and physical properties of gelatin extracted from pangasius catfish (*Pangasius sutchi*) bone, *J. Food Sci. Technol.* 51 (2014) 3104–3113, <https://doi.org/10.1007/s13197-012-0816-7>.
 - [54] A.V. Sanaei, F. Mahmoodani, S.F. See, S.M. Yusop, A.S. Babji, Optimization of gelatin extraction and physico-chemical properties of catfish (*Clarias gariepinus*) bone gelatin, *Int. Food Res. J.* 20 (2013) 423–430.
 - [55] R. Jeya Shakila, E. Jeevithan, A. Varatharajakumar, G. Jeyasekaran, D. Sukumar, Functional characterization of gelatin extracted from bones of red snapper and grouper in comparison with mammalian gelatin, *Lwt* 48 (2012) 30–36, <https://doi.org/10.1016/j.lwt.2012.03.007>.
 - [56] A. Taheri, A.M. Abedian Kenari, A. Gildberg, S. Behnam, Extraction and physicochemical characterization of greater lizardfish (*Saurida tumbil*) skin and bone gelatin, *J. Food Sci.* 74 (2009), <https://doi.org/10.1111/j.1750-3841.2009.01106.x>.
 - [57] M. Pertiwi, Y. Atma, A. Mustopa, R. Maisarah, Karakteristik fisik dan kimia gelatin dari tulang ikan Patin dengan pre-treatment asam sitrat, *J. Apl. Teknol. Pangan* 7 (2018) 83–91, <https://doi.org/10.17728/jatp.2470>.
 - [58] H.A. Monsur, I. Jaswir, H.M. Salleh, H.A. Alkahtani, Effects of pretreatment on properties of gelatin from perch (*Lates niloticus*) skin, *Int. J. Food Prop.* 17 (2014) 1224–1236, <https://doi.org/10.1080/10942912.2012.685676>.
 - [59] S.F. See, P.K. Hong, K.L. Ng, W.M. Wan Aida, A.S. Babji, Physicochemical properties of gelatins extracted from skins of different freshwater fish species, *Int. Food Res. J.* 17 (2010) 809–816.
 - [60] J.M. Koli, S. Basu, B.B. Nayak, S.B. Patange, A.U. Pagarkar, V. Gudipati, Functional characteristics of gelatin extracted from skin and bone of Tiger-toothed croaker (*Otolithes ruber*) and Pink perch (*Nemipterus japonicus*), *Food Bioprod. Process.* 90 (2012) 555–562, <https://doi.org/10.1016/j.fbp.2011.08.001>.
 - [61] K. Shyni, G.S. Hema, G. Ninan, S. Mathew, C.G. Joshy, P.T. Lakshmanan, Isolation and characterization of gelatin from the skins of skipjack tuna (*Katsuwonus pelamis*), dog shark (*Scoliodon sorrakowah*), and rohu (*Labeo rohita*), *Food Hydrocolloids* 39 (2014) 68–76, <https://doi.org/10.1016/j.foodhyd.2013.12.008>.
 - [62] A. Mirzapour-Kouhdasht, F. Sabzipour, M.S. Taghizadeh, M. Moosavi-Nasab, Physicochemical, rheological, and molecular characterization of colloidal gelatin produced from Common carp by-products using microwave and ultrasound-assisted extraction, *J. Texture Stud.* 50 (2019) 416–425, <https://doi.org/10.1111/jtxs.12408>.
 - [63] Y. Atma, M. Taufik, Physico-chemical properties gelatin from bone of pangasius sutchi extracted with citrus fruits, *Biointerface Res. Appl. Chem.* 11 (2021) 11509–11518, <https://doi.org/10.33263/BRIAC114.1150911518>.
 - [64] H.Y. Fan, M.J. Dumont, B.K. Simpson, Extraction of gelatin from salmon (*Salmo salar*) fish skin using trypsin-aided process: optimization by Plackett–Burman and response surface methodological approaches, *J. Food Sci. Technol.* 54 (2017) 4000–4008, <https://doi.org/10.1007/s13197-017-2864-5>.
 - [65] S.R. Derkach, N.G. Voron'ko, Y.A. Kuchina, D.S. Kolotova, Modified fish gelatin as an alternative to mammalian gelatin in modern food technologies, *Polymers* 12 (2020) 1–10, <https://doi.org/10.3390/polym12123051>.
 - [66] Y. Atma, Amino acid and proximate composition of fish bone gelatin from different warm-water species: a comparative study, *IOP Conf. Ser. Earth Environ. Sci.* 58 (2017) 012008, <https://doi.org/10.1088/1755-1315/58/1/012008>.
 - [67] F. Mahmoodani, V.S. Ardekani, S.S. Fern, S.M. Yusop, A.S. Babji, Optimization of extraction and physicochemical properties of gelatin from pangasius catfish (*Pangasius sutchi*) skin, *Sains Malays.* 43 (2014) 995–1002.
 - [68] L. Yang, M. Yang, J. Xu, Y. Nie, W. Wu, T. Zhang, X. Wang, J. Zhong, Structural and emulsion stabilization comparison of four gelatins from two freshwater and two marine fish skins, *Food Chem.* 371 (2022) 131129, <https://doi.org/10.1016/j.foodchem.2021.131129>.
 - [69] A.L. Alves, F.J. Fraguas, A.C. Carvalho, J. Valcárcel, R.I. Pérez-Martín, R.L. Reis, J.A. Vázquez, T.H. Silva, Characterization of codfish gelatin: a comparative study of fresh and salted skins and different extraction methods, *Food Hydrocolloids* 124 (2022), <https://doi.org/10.1016/j.foodhyd.2021.107238>.
 - [70] V. Renuka, C.N. Rao Ravishankar, A.A. Zynuddeen, J. Bindu, T.C. Joseph, Characterization of gelatin obtained from unicorn leatherjacket (*Aluterus monoceros*) and reef cod (*Epinephelus diacanthus*) skins, *Lwt* 116 (2019) 108586, <https://doi.org/10.1016/j.lwt.2019.108586>.
 - [71] I. Ratnasari, S.S. Yuwono, H. Nusyam, S.B. Widjanarko, Extraction and characterization of gelatin from different fresh water fishes as alternative sources of gelatin, *Int. Food Res. J.* 20 (2013) 3085–3091.
 - [72] A. da T. Alfaro, E. Balbinot, C.I. Weber, I.B. Tonial, A. Machado-Lunkes, Fish gelatin: characteristics, functional properties, applications and future potentials, *Food Eng. Rev.* 7 (2015) 33–44, <https://doi.org/10.1007/s12393-014-9096-5>.
 - [73] F. Zhang, S. Xu, Z. Wang, Pre-treatment optimization and properties of gelatin from freshwater fish scales, *Food Bioprod. Process.* 89 (2011) 185–193, <https://doi.org/10.1016/j.fbp.2010.05.003>.
 - [74] Y. Wang, J.M. Regenstein, Effect of EDTA, HCl, and citric acid on Ca salt removal from Asian (silver) carp scales prior to gelatin extraction, *J. Food Sci.* 74 (2009), <https://doi.org/10.1111/j.1750-3841.2009.01202.x>.
 - [75] L. Niu, X. Zhou, C. Yuan, Y. Bai, K. Lai, F. Yang, Y. Huang, Characterization of tilapia (*Oreochromis niloticus*) skin gelatin extracted with alkaline and different acid pretreatments, *Food Hydrocolloids* 33 (2013) 336–341, <https://doi.org/10.1016/j.foodhyd.2013.04.014>.
 - [76] S.M. Cho, Y.S. Gu, S.B. Kim, Extracting optimization and physical properties of yellowfin tuna (*Thunnus albacares*) skin gelatin compared to mammalian gelatins, *Food Hydrocolloids* 19 (2005) 221–229, <https://doi.org/10.1016/j.foodhyd.2004.05.005>.
 - [77] J.A. Arnesen, A. Gildberg, Extraction and characterisation of gelatine from Atlantic salmon (*Salmo salar*) skin, *Bioresour. Technol.* 98 (2007) 53–57, <https://doi.org/10.1016/j.biortech.2005.11.021>.

- [78] S. Wangtueai, A. Noomhorm, Processing optimization and characterization of gelatin from lizardfish (*Saurida* spp.) scales, *Lwt* 42 (2009) 825–834, <https://doi.org/10.1016/j.lwt.2008.11.014>.
- [79] K.A. Pradarameswari, K. Zaelani, E. Waluyo, R. Nurdiani, The physico-chemical properties of pangas catfish (*Pangasius pangasius*) skin gelatin, *IOP Conf. Ser. Earth Environ. Sci.* 137 (2018), <https://doi.org/10.1088/1755-1315/137/1/012067>.
- [80] Y. Atma, H. Ramdhani, A.Z. Mustopa, M. Pertiwi, R. Maisarah, Karakteristik fisikokimia gelatin tulang ikan Patin (*Pangasius sutchi*) hasil ekstraksi menggunakan limbah buah nanas (*Ananas comosus*), *Agritech* 38 (2018) 56, <https://doi.org/10.22146/agritech.29821>.
- [81] N. Azizah, Y. Ochiai, M. Nurilmala, Collagen peptides from Pangasius fish skin as antioxidants, *IOP Conf. Ser. Earth Environ. Sci.* 404 (2019), <https://doi.org/10.1088/1755-1315/404/1/012055>.
- [82] Q. Zhang, Q. Wang, S. Lv, J. Lu, S. Jiang, J.M. Regenstein, L. Lin, Comparison of collagen and gelatin extracted from the skins of Nile tilapia (*Oreochromis niloticus*) and channel catfish (*Ictalurus punctatus*), *Food Biosci.* 13 (2016) 41–48, <https://doi.org/10.1016/j.fbio.2015.12.005>.
- [83] N. Ismail, W.N.F. Wan A. Latiff, Effect of pre-treatment on physical properties and sensory attributes of gelatin extracted from sutchi catfish (*Pangasius sutchi*) skin, *Sci. Res. J.* 16 (2019) 59, <https://doi.org/10.24191/srj.v16i2.6175>.
- [84] S. Suparmi, E. Edison, M. Meivayana, Processing of gelatin from the skin of pangasius hypophthalmus using papain enzyme, *IOP Conf. Ser. Earth Environ. Sci.* 934 (2021), <https://doi.org/10.1088/1755-1315/934/1/012094>.
- [85] M. Nurilmala, D. Sriwahyuni, R. Nugraha, V. Ridzha Kartika, N. Darmawan, E. Apriliani Wulandari Putri, A. Wirabudi Pranata, Y. Ochiai, Response surface methodology (RSM) for optimization of gelatin extraction from pangasius fish skin and its utilization for hard capsules, *Arab. J. Chem.* 16 (2023) 104938, <https://doi.org/10.1016/j.arabjc.2023.104938>.
- [86] I.D. Asih, T. Kemala, M. Nurilmala, Halal gelatin extraction from Patin fish bone (*Pangasius hypophthalmus*) by-product with ultrasound-assisted extraction, *IOP Conf. Ser. Earth Environ. Sci.* 299 (2019), <https://doi.org/10.1088/1755-1315/299/1/012061>.
- [87] I. Akbar, I. Jaswir, P. Jamal, Optimisation of the production of fish gelatine nanoparticles as a carrier for sunflower-derived biopeptide, *Int. Food Res. J.* 27 (2020) 171–181.
- [88] D. Subara, I. Jaswir, M.F.R. Alkhatib, I.A.N. Noorbata, Process optimization for the production of fish gelatin nanoparticles, *Int. Food Res. J.* 24 (2017) 501–507.
- [89] L. Zhang, A. Liu, W. Wang, R. Ye, Y. Liu, J. Xiao, K. Wang, Characterisation of microemulsion nanofilms based on Tilapia fish skin gelatine and ZnO nanoparticles incorporated with ginger essential oil: meat packaging application, *Int. J. Food Sci. Technol.* 52 (2017) 1670–1679, <https://doi.org/10.1111/ijfs.13441>.
- [90] N.M. Hani, A.E. Torkamani, M.H. Azarian, K.W.A. Mahmood, S.H. Ngalm, Characterisation of electrospun gelatine nanofibres encapsulated with *Moringa oleifera* bioactive extract, *J. Sci. Food Agric.* 97 (2017) 3348–3358, <https://doi.org/10.1002/jsfa.8185>.
- [91] Y.A. Arfat, S. Benjakul, K. Vongkamjan, P. Sumpavapool, S. Yarnpakdee, Shelf-life extension of refrigerated sea bass slices wrapped with fish protein isolate/fish skin gelatin-ZnO nanocomposite film incorporated with basil leaf essential oil, *J. Food Sci. Technol.* 52 (2015) 6182–6193, <https://doi.org/10.1007/s13197-014-1706-y>.
- [92] M. Nuerjiang, X. Bai, L. Sun, Q. Wang, X. Xia, F. Li, Size effect of fish gelatin nanoparticles on the mechanical properties of collagen film based on its hierarchical structure, *Food Hydrocolloids* 144 (2023) 108931, <https://doi.org/10.1016/j.foodhyd.2023.108931>.
- [93] P.K. Dara, M. Raghavankutty, G. Balaraman, P.M. Ashraf, S. Visnuvinayagam, C. S. Tejpal, S. Mathew, R.C. Nagarajao, A. Rangasamy, Biocompatibility and histopathological evaluation of chitosan nanoparticles grafted fish gelatin bio-nanocomposite membranes in rats, *Iran. Polym. J. (English Ed.)* 30 (2021) 953–964, <https://doi.org/10.1007/s13726-021-00947-4>.
- [94] P. Khramtsov, O. Burdina, S. Lazarev, A. Novokshonova, M. Bochkova, V. Timanova, D. Kiselkov, A. Minin, S. Zamorina, M. Rayev, Modified desolvation method enables simple one-step synthesis of gelatin nanoparticles from different gelatin types with any bloom values, *Pharmaceutics* 13 (2021) 1–26, <https://doi.org/10.3390/pharmaceutics13101537>.
- [95] H. Chen, S. Lin, J. Wu, Y. Xu, X. Cai, S. Wang, The structure, antioxidant activity, and stability of fish gelatin/chitosan oligosaccharide nanoparticles loaded with apple polyphenols, *J. Sci. Food Agric.* 103 (2023) 4211–4220, <https://doi.org/10.1002/jsfa.12455>.
- [96] H.W. Kwak, M. Shin, J.Y. Lee, H. Yun, D.W. Song, Y. Yang, B.S. Shin, Y.H. Park, K. H. Lee, Fabrication of an ultrafine fish gelatin nanofibrous web from an aqueous solution by electrospinning, *Int. J. Biol. Macromol.* 102 (2017) 1092–1103, <https://doi.org/10.1016/j.ijbiomac.2017.04.087>.
- [97] S.F. Hosseini, M. Rezaei, M. Zandi, F. Farahmandghavi, Development of bioactive fish gelatin/chitosan nanoparticles composite films with antimicrobial properties, *Food Chem.* 194 (2016) 1266–1274, <https://doi.org/10.1016/j.foodchem.2015.09.004>.
- [98] S.J. Wu, Y.C. Ho, S.Z. Jiang, F.L. Mi, Effect of tannic acid-fish scale gelatin hydrolysate hybrid nanoparticles on intestinal barrier function and α -amylase activity, *Food Funct.* 6 (2015) 2283–2292, <https://doi.org/10.1039/c4fo01015a>.
- [99] D. Subara, I. Jaswir, M.F. Rashid Alkhatib, I.A. Noorbata, Understanding the significance variables for fabrication of fish gelatin nanoparticles by Plackett-Burman design, *IOP Conf. Ser. Mater. Sci. Eng.* 290 (2018), <https://doi.org/10.1088/1757-899X/290/1/012006>.
- [100] T. Sinha, M. Ahmaruzzaman, A.K. Sil, A. Bhattacharjee, Biomimetic synthesis of silver nanoparticles using the fish scales of *Labeo rohita* and their application as catalysts for the reduction of aromatic nitro compounds, *Spectrochim. Acta Part A Mol. Biomol. Spectrosc.* 131 (2014) 413–423, <https://doi.org/10.1016/j.saa.2014.04.065>.
- [101] J. Rouhi, S. Mahmud, N. Naderi, C.H. Raymond Ooi, M.R. Mahmood, Physical properties of fish gelatin-based bio-nanocomposite films incorporated with ZnO nanorods, *Nanoscale Res. Lett.* 8 (2013) 1–6, <https://doi.org/10.1186/1556-276X-8-364>.
- [102] Y.A. Arfat, J. Ahmed, N. Hiremath, R. Auras, A. Joseph, Thermo-mechanical, rheological, structural and antimicrobial properties of bionanocomposite films based on fish skin gelatin and silver-copper nanoparticles, *Food Hydrocolloids* 62 (2017) 191–202, <https://doi.org/10.1016/j.foodhyd.2016.08.009>.
- [103] Y.A. Arfat, S. Benjakul, T. Prodpran, P. Sumpavapool, P. Songtipya, Physico-mechanical characterization and antimicrobial properties of fish protein isolate/fish skin gelatin-zinc oxide (ZnO) nanocomposite films, *Food Bioprocess Technol.* 9 (2016) 101–112, <https://doi.org/10.1007/s11947-015-1602-0>.
- [104] S.F. Hosseini, M. Rezaei, M. Zandi, F. Farahmandghavi, Fabrication of bio-nanocomposite films based on fish gelatin reinforced with chitosan nanoparticles, *Food Hydrocolloids* 44 (2015) 172–182, <https://doi.org/10.1016/j.foodhyd.2014.09.004>.
- [105] J. Chen, L. Luo, C. Cen, Y. Liu, H. Li, Y. Wang, The nano antibacterial composite film carboxymethyl chitosan/gelatin/nano ZnO improves the mechanical strength of food packaging, *Int. J. Biol. Macromol.* 220 (2022) 462–471, <https://doi.org/10.1016/j.ijbiomac.2022.08.005>.
- [106] J.B. Aswathanarayan, R.R. Vittal, Nanoemulsions and their potential applications in food industry, *Front. Sustain. Food Syst.* 3 (2019) 1–21, <https://doi.org/10.3389/fsufs.2019.00095>.
- [107] S. Aththanayaka, G. Thiripuranathar, S. Ekanayake, Emerging advances in biomimetic synthesis of nanocomposites and potential applications, *Mater. Today Sustain.* 20 (2022), <https://doi.org/10.1016/j.mtsust.2022.100206>.
- [108] Y. He, M. Cheng, R. Yang, H. Li, Z. Lu, Y. Jin, J. Feng, L. Tu, Research progress on the mechanism of nanoparticles crossing the intestinal epithelial cell membrane, *Pharmaceutics* 15 (2023) 1–18, <https://doi.org/10.3390/pharmaceutics15071816>.
- [109] A. O'Connell, F.M. Goycoolea, A. Gulotta, P. Holmqvist, P. Schuetz, J. Mattsson, The structure and dynamics of locust bean gum in aqueous solution, *Food Hydrocolloids* 138 (2023) 108446, <https://doi.org/10.1016/j.foodhyd.2022.108446>.
- [110] S. kazemi, A. Hosseiniholian, S.D. Gohari, F. Feirahi, F. Moammeri, G. Mesbahian, Z.S. Moghaddam, Q. Ren, Recent advances in green synthesized nanoparticles: from production to application, *Mater. Today Sustain.* 24 (2023) 100500, <https://doi.org/10.1016/j.mtsust.2023.100500>.
- [111] L. Pravinata, M. Akhtar, P.J. Bentley, T. Mahatnirunkul, B.S. Murray, Preparation of alginate microgels in a simple one step process via the Leeds Jet Homogenizer, *Food Hydrocolloids* 61 (2016) 77–84, <https://doi.org/10.1016/j.foodhyd.2016.04.025>.
- [112] J. Stetefeld, S.A. McKenna, T.R. Patel, Dynamic light scattering: a practical guide and applications in biomedical sciences, *Biophys. Rev.* 8 (2016) 409–427, <https://doi.org/10.1007/s12551-016-0218-6>.
- [113] C. Arnoth, A Study of Protein Aggregation Processes Using Dynamic Light Scattering, 2020.
- [114] N. Raval, R. Maheshwari, D. Kalyane, S.R. Youngren-Ortiz, M.B. Chougule, R. K. Tekade, Importance of Physicochemical Characterization of Nanoparticles in Pharmaceutical Product Development, Elsevier Inc., 2019, <https://doi.org/10.1016/B978-0-12-817909-3.00010-8>.
- [115] D. Gazzino, R. Fantoni, A. Giacometti, Phase behaviour of polydisperse sticky hard spheres: analytical solutions and perturbation theory, *Mol. Phys.* 104 (2006) 3451–3459, <https://doi.org/10.1080/00268970601050892>.
- [116] T. Mudalige, H. Qu, D. Van Haute, S.M. Ansar, A. Paredes, T. Ingle, Characterization of Nanomaterials: Tools and Challenges, Elsevier Inc., 2019, <https://doi.org/10.1016/B978-0-12-814130-4.00011-7>.
- [117] U. Nobbmann, M. Connah, B. Fish, P. Varley, C. Gee, S. Mulot, J. Chen, L. Zhou, Y. Lu, F. Sheng, J. Yi, S.E. Harding, Dynamic light scattering as a relative tool for assessing the molecular integrity and stability of monoclonal antibodies, *Biotechnol. Genet. Eng. Rev.* 24 (2007) 117–128, <https://doi.org/10.1080/02648725.2007.10648095>.
- [118] J.N. Weiss, Dynamic light scattering (DLS) spectroscopy, in: *Dyn. Light Scatt. Spectrosc. Hum. Eye*, Springer International Publishing, Cham, 2022, pp. 13–17.
- [119] R. Liu, Z. Fu, Y. Yuying, Preparation and evaluation of stable nanofluids for heat transfer application, *Adv. Nanofluid Heat Transf.* (2022) 25–57.
- [120] J.C. Thomas, B.J. Crosby, R.I. Keir, K.L. Hanton, Observation of field-dependent electrophoretic mobility with phase analysis light scattering (PALS), *Langmuir* 18 (2002) 4243–4247, <https://doi.org/10.1021/la011758e>.
- [121] F. McNeil-Watson, W.W. Tschamruter, J. Miller, A new instrument for the measurement of very small electrophoretic mobilities using phase analysis light scattering, *Colloids Surfaces A Physicochem. Eng. Asp.* 140 140 (1998) 53–57, <https://doi.org/10.1021/bk-1998-0693.ch023>.
- [122] A. Sze, D. Erickson, L. Ren, D. Li, Zeta-potential measurement using the Smoluchowski equation and the slope of the current-time relationship in electroosmotic flow, *J. Colloid Interface Sci.* 261 (2003) 402–410, [https://doi.org/10.1016/S0021-9797\(03\)00142-5](https://doi.org/10.1016/S0021-9797(03)00142-5).
- [123] A. Doroszowski, The Physical Chemistry of Dispersion, second ed., Woodhead Publishing Ltd, 1999 <https://doi.org/10.1533/9781855737006.198>.

- [124] K. Hattar, K.L. Jungjohann, Possibility of an integrated transmission electron microscope: enabling complex in-situ experiments, *J. Mater. Sci.* 56 (2021) 5309–5320, <https://doi.org/10.1007/s10853-020-05598-z>.
- [125] R. Brydson, A. Brown, L.G. Benning, K. Livy, Analytical transmission electron microscopy, *Reviews in Mineralogy and Geochemistry*, Rev. Mineral. Geochemistry 78 (2014). <http://eprints.whiterose.ac.uk/80230/>.
- [126] M. Malkoch, E. Malmström, A.M. Nyström, 6.04 - Dendrimers: Properties and Applications, Elsevier B.V., 2012, <https://doi.org/10.1016/B978-0-444-53349-4.00162-X>.
- [127] S.J. Pennycook, Transmission electron microscopy, in: Bancroft's Theory Pract. Histol. Tech, Seventh, 2012, pp. 493–538, <https://doi.org/10.1016/B978-0-7020-4226-3.00022-6>.
- [128] J. Gómez-Estaca, M.C. Gómez-Guillén, F. Fernández-Martín, P. Montero, Effects of gelatin origin, bovine-hide and tuna-skin, on the properties of compound gelatin-chitosan films, *Food Hydrocolloids* 25 (2011) 1461–1469, <https://doi.org/10.1016/j.foodhyd.2011.01.007>.
- [129] V. Kovacevic, D. Vrsaljko, S.L. Blagojevic, M. Leskovic, Adhesion parameters at the interface in nanoparticle filled polymer systems vera, *Polym. Eng. Sci.* 48 (2008) 1994–2002, <https://doi.org/10.1002/pen>.
- [130] M. Corrales, A. Fernández, J.H. Han, Antimicrobial Packaging Systems, 2013, <https://doi.org/10.1016/B978-0-12-394601-0.00007-2>.
- [131] S. Burt, Essential oils: their antibacterial properties and potential applications in foods - a review, *Int. J. Food Microbiol.* 94 (2004) 223–253, <https://doi.org/10.1016/j.jfoodmicro.2004.03.022>.
- [132] A. Ultee, M.H.J. Bennik, R. Moezelaar, The phenolic hydroxyl group of carvacrol is essential for action against the food-borne pathogen *Bacillus cereus*, *Appl. Environ. Microbiol.* 68 (2002) 1561–1568, <https://doi.org/10.1128/AEM.68.4.1561-1568.2002>.
- [133] K.Y. Lee, J.H. Lee, H.J. Yang, K. Bin Song, Production and characterisation of skate skin gelatin films incorporated with thyme essential oil and their application in chicken tenderloin packaging, *Int. J. Food Sci. Technol.* 51 (2016) 1465–1472, <https://doi.org/10.1111/ijfs.13119>.
- [134] Y.A. Arfat, S. Benjakul, T. Prodpran, P. Sumpavapol, P. Songtipya, Properties and antimicrobial activity of fish protein isolate/fish skin gelatin film containing basil leaf essential oil and zinc oxide nanoparticles, *Food Hydrocolloids* 41 (2014) 265–273, <https://doi.org/10.1016/j.foodhyd.2014.04.023>.
- [135] F. Shahmohammadi Jebel, H. Almasi, Morphological, physical, antimicrobial and release properties of ZnO nanoparticles-loaded bacterial cellulose films, *Carbohydr. Polym.* 149 (2016) 8–19, <https://doi.org/10.1016/j.carbpol.2016.04.089>.
- [136] H. Yang, Y. Wang, P. Zhou, J.M. Regenstein, Effects of alkaline and acid pretreatment on the physical properties and nanostructures of the gelatin from channel catfish skins, *Food Hydrocolloids* 22 (2008) 1541–1550, <https://doi.org/10.1016/j.foodhyd.2007.10.007>.
- [137] A.A. Tayel, W.F. El-Tras, S. Moussa, A.F. El-Baz, H. Mahrous, M.F. Salem, L. Brimer, Antibacterial action of zinc oxide nanoparticles against foodborne pathogens, *J. Food Saf.* 31 (2011) 211–218, <https://doi.org/10.1111/j.1745-4565.2010.00287.x>.
- [138] S. Anitha, B. Brabu, D.J. Thiruvadigal, C. Gopalakrishnan, T.S. Natarajan, Preparation of Free-Standing Electrospun Composite ZnO Membrane for Antibacterial Applications, vol. 5, 2012, pp. 468–474, <https://doi.org/10.1166/asl.2012.1981>.
- [139] S. Pal, Y.K. Tak, J.M. Song, Does the antibacterial activity of silver nanoparticles depend on the shape of the nanoparticle? A study of the gram-negative bacterium *Escherichia coli*, *Appl. Environ. Microbiol.* 73 (2007) 1712–1720, <https://doi.org/10.1128/AEM.02218-06>.
- [140] S.M. Dizaj, F. Lotfipour, M. Barzegar-Jalali, M.H. Zarrintan, K. Adibkia, Antimicrobial activity of the metals and metal oxide nanoparticles, *Mater. Sci. Eng. C* 44 (2014) 278–284, <https://doi.org/10.1016/j.msec.2014.08.031>.
- [141] B. Fu, S. Mei, X. Su, H. Chen, J. Zhu, Z. Zheng, H. Lin, C. Dai, R. Luque, D.-P. Yang, Integrating waste fish scale-derived gelatin and chitosan into edible nanocomposite film for perishable fruits, *Int. J. Biol. Macromol.* 191 (2021) 1164–1174, <https://doi.org/10.1016/j.ijbiomac.2021.09.171>.
- [142] A.K. Bajpai, J. Choubey, Design of gelatin nanoparticles as swelling controlled delivery system for chloroquine phosphate, *J. Mater. Sci. Mater. Med.* 17 (2006) 345–358, <https://doi.org/10.1007/s10856-006-8235-9>.
- [143] J. Choubey, A.K. Bajpai, Investigation on magnetically controlled delivery of doxorubicin from superparamagnetic nanocarriers of gelatin crosslinked with genipin, *J. Mater. Sci. Mater. Med.* 21 (2010) 1573–1586, <https://doi.org/10.1007/s10856-010-3997-5>.
- [144] A.K. Gupta, M. Gupta, S.J. Yarwood, A.S.G. Curtis, Effect of cellular uptake of gelatin nanoparticles on adhesion, morphology and cytoskeleton organisation of human fibroblasts, *J. Contr. Release* 95 (2004) 197–207, <https://doi.org/10.1016/j.jconrel.2003.11.006>.
- [145] S.A. Khan, M. Schneider, Improvement of nanoprecipitation technique for preparation of gelatin nanoparticles and potential macromolecular drug loading, *Macromol. Biosci.* 13 (2013) 455–463, <https://doi.org/10.1002/mabi.201200382>.
- [146] E.J. Lee, S.A. Khan, J.K. Park, K.H. Lim, Studies on the characteristics of drug-loaded gelatin nanoparticles prepared by nanoprecipitation, *Bioproc. Biosyst. Eng.* 35 (2012) 297–307, <https://doi.org/10.1007/s00449-011-0591-2>.
- [147] Z. Li, L. Gu, Effects of mass ratio, pH, temperature, and reaction time on fabrication of partially purified pomegranate ellagitannin-gelatin nanoparticles, *J. Agric. Food Chem.* 59 (2011) 4225–4231, <https://doi.org/10.1021/jf200024d>.
- [148] Y.C. Chen, S.H. Yu, G.J. Tsai, D.W. Tang, F.L. Mi, Y.P. Peng, Novel technology for the preparation of self-assembled Catechin/Gelatin nanoparticles and their characterization, *J. Agric. Food Chem.* 58 (2010) 6728–6734, <https://doi.org/10.1021/jf1005116>.
- [149] R. Yasmin, M. Shah, S.A. Khan, R. Ali, Gelatin nanoparticles: a potential candidate for medical applications, *Nanotechnol. Rev.* 6 (2017) 191–207, <https://doi.org/10.1515/ntrev-2016-0009>.
- [150] N. Sahoo, R.K. Sahoo, N. Biswas, A. Guha, K. Kuotsu, Recent advancement of gelatin nanoparticles in drug and vaccine delivery, *Int. J. Biol. Macromol.* 81 (2015) 317–331, <https://doi.org/10.1016/j.ijbiomac.2015.08.006>.
- [151] R.M. Hathout, A.A. Metwally, Gelatin Nanoparticles, 2019, https://doi.org/10.1007/978-1-4939-9516-5_8.
- [152] A. Pavlicek, F. Part, G. Rose, A. Praetorius, M. Miernicki, A. Gazsó, M. Huber-Humer, A European nano-registry as a reliable database for quantitative risk assessment of nanomaterials? a comparison of national approaches, *NanoImpact* 21 (2021), <https://doi.org/10.1016/j.impact.2020.100276>.
- [153] Y. Lugani, B.S. Sooch, P. Singh, S. Kumar, 8 - Nanobiotechnology applications in food sector and future innovations, *Microb. Biotechnol. Food Heal.* (2021) 197–225.
- [154] J.K. Jakhar, S. Basu, S. Sasidharan, M.K. Chouksey, V. Gudipati, Optimization of process parameters for gelatin extraction from the skin of Blackspotted croaker using response surface methodology, *J. Food Sci. Technol.* 51 (2014) 3235–3243, <https://doi.org/10.1007/s13197-012-0883-9>.
- [155] M. Nasrallah, P. Ghossi, J.E. Spradlin, J.R. Magnifico, Extraction process for gelatin 5210182, US, 1993.
- [156] A. Maihemuti, H. Zhang, X. Lin, Y. Wang, Z. Xu, D. Zhang, Q. Jiang, 3D-printed fish gelatin scaffolds for cartilage tissue engineering, *Bioact. Mater.* 26 (2023) 77–87, <https://doi.org/10.1016/j.bioactmat.2023.02.007>.
- [157] L.C. Sow, N.Z.Y. Toh, C.W. Wong, H. Yang, Combination of sodium alginate with tilapia fish gelatin for improved texture properties and nanostructure modification, *Food Hydrocolloids* 94 (2019) 459–467, <https://doi.org/10.1016/j.foodhyd.2019.03.041>.
- [158] D. Lin, Y. Yang, J. Wang, W. Yan, Z. Wu, H. Chen, Q. Zhang, D. Wu, W. Qin, Z. Tu, Preparation and characterization of TiO₂-Ag loaded fish gelatin-chitosan antibacterial composite film for food packaging, *Int. J. Biol. Macromol.* 154 (2020) 123–133, <https://doi.org/10.1016/j.ijbiomac.2020.03.070>.
- [159] J. Uranga, A.I. Puertas, A. Etxabide, M.T. Duenas, P. Guerrero, K. de la Caba, Citric acid-incorporated fish gelatin/chitosan composite films, *Food Hydrocolloids* 86 (2019) 95–103, <https://doi.org/10.1016/j.foodhyd.2018.02.018>.
- [160] E.T. Aksun Tümerkan, L.D. Kozaci, A.K. Miri, S. Maharjan, B. Cecen, Sustainable aquatic waste and by-products processing: biomaterials in tissue engineering facts and gaps, *Mater. Today Sustain* 23 (2023) 100445, <https://doi.org/10.1016/j.mtsust.2023.100445>.
- [161] G.C. Demir, Ö. Erdemli, D. Keskin, A. Tezcaner, Xanthan-gelatin and xanthan-gelatin-keratin wound dressings for local delivery of Vitamin C, *Int. J. Pharm.* 614 (2022), <https://doi.org/10.1016/j.ijpharm.2021.121436>.
- [162] Y. Atma, Synthesis and application of fish gelatin for hydrogels/composite hydrogels: a review, *Biointerface Res. Appl. Chem.* 12 (2022) 3966–3976, <https://doi.org/10.33263/BR1AC123.39663976>.
- [163] L.C. de Oliveira, J.R. Barbosa, S. da C.A. Ribeiro, M.A.M. de Vasconcelos, B.A. de Aguiar, G.V. da S. Pereira, G.A. Albuquerque, F.N.L. da Silva, R.L. Crizel, P. H. Campelo, L. de F.H. Lourenço, Improvement of the characteristics of fish gelatin – gum Arabic through the formation of the polyelectrolyte complex, *Carbohydr. Polym.* 223 (2019) 115068, <https://doi.org/10.1016/j.carbpol.2019.115068>.
- [164] B.C. da Silva, M. de Oliveira, J.G.L. Ferreira, M.R. Sierakowski, F.F. Simas-Tosin, E.S. Orth, I.C. Riegel-Vidotti, Polyelectrolyte complexes from gum Arabic and gelatin: optimal complexation pH as a key parameter to obtain reproducible microcapsules, *Food Hydrocolloids* 46 (2015) 201–207, <https://doi.org/10.1016/j.foodhyd.2014.12.022>.
- [165] H. Ehtesabi, M. Fayaz, F. Hosseini-Doabi, P. Rezaei, The application of green synthesis nanoparticles in wound healing: a review, *Mater. Today Sustain.* 21 (2023) 100272, <https://doi.org/10.1016/j.mtsust.2022.100272>.
- [166] S. Talebian, T. Rodrigues, J. Das Neves, B. Sarmento, R. Langer, J. Conde, Facts and figures on materials science and nanotechnology progress and investment, *ACS Nano* 15 (2021) 15940–15952, <https://doi.org/10.1021/acsnano.1c03992>.
- [167] P. Laux, J. Tentschert, C. Riebeling, A. Braeuning, O. Creutzenberg, A. Epp, V. Fessard, K.H. Haas, A. Haase, K. Hund-Rinke, N. Jakubowski, P. Kearns, A. Lampen, H. Rauscher, R. Schoonjans, A. Störmer, A. Thielmann, U. Mühle, A. Luch, Nanomaterials: certain aspects of application, risk assessment and risk communication, *Arch. Toxicol.* 92 (2018) 121–141, <https://doi.org/10.1007/s00204-017-2144-1>.
- [168] J. Guerra-Garcés, C.A. García-Negrete, K. Pastor-Sierra, G.C. Arteaga, M. Barrera-Vargas, M.C. Jiménez de Haro, A. Fernández, Morphologically diverse CaCO₃ microparticles and their incorporation into recycled cellulose for circular economy, *Mater. Today Sustain.* 19 (2022), <https://doi.org/10.1016/j.mtsust.2022.100166>.